

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

Foreword

The European chemical and polymer industry is using a large amount of wooden pallets for the distribution of goods. For environmental, quality and safety reasons there is a strong need to organise the use and re-use of these pallets.

Within PlasticsEurope, a team of experts from various chemicals and plastics producing companies, together with pallet specialists, have developed in the early '90 a standard for wooden pallets and drafted the present manufacturing and reconditioning specifications of the Chemical industry Pallets, called CP pallets. Special attention has been paid to quality, safety and environmental aspects.

Although CP pallets have been designed for specific packages commonly used within the chemical and polymer industry, they are also suitable for other loads. Tests performed by various companies and testing institutes and experience from the use and re-use of millions of CP's since 1991 have demonstrated that they conform to the needs of the chemical and polymer industry and their customers. However, PlasticsEurope Services cannot be held responsible for any problems or liabilities which may result from the use of the CP pallets system.

Scope

This document describes the pallet supplier registration and the system to collect used CP pallets. It defines the CP manufacturing, reconditioning and quality assurance criteria. It informs about the safe working load of CP's.

Correspondence can be addressed to:



Rue Belliard 40, Box 16, 1040 Brussels (Belgium)

patrick.dhose@plasticseuropeservices.eu

www.plasticseurope.org

Note: The content of this document is not essentially different from the previous edition, but has been completed with clarifications about the Supplier registration (header A.) and Marking (header B. 3.3.6).

This edition 7 annuls and replaces the previous edition 6 dated April 2004.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

Contents

A.	Supplier registration	3
B.	Manufacturing specification.....	3
1.	Scope	3
2.	Normative references.....	4
3.	Construction	5
3.1.	Materials requirements.....	5
3.1.1.	Sawn timber	5
3.1.1.1.	Wood species	5
3.1.1.2.	Quality.....	5
3.1.1.3.	Moisture content	6
3.1.1.4.	Packaging issues related to wet timber [informative]	6
3.1.2.	Particleboard blocks [optional]	7
3.1.3.	Plastic blocks [optional].....	7
3.1.4.	Fasteners	8
3.2.	Dimensions.....	8
3.2.1.	Pallet dimensions & permitted deviations	8
3.2.2.	Permitted deviations of component parts made of sawn green timber.....	8
3.2.3.	Permitted timber dimensions considering moisture content	9
3.3.	Manufacturing requirements.....	9
3.3.1.	Component parts.....	9
3.3.2.	Assembly.....	9
3.3.3.	Joints	10
3.3.4.	Bottom board chamfer [optional]	10
3.3.5.	Finishing	11
3.3.6.	Marking.....	11
C.	Collection of used CP's	12
D.	Reconditioning specification.....	12
1.	Scope	12
2.	Unacceptable deficiencies	12
3.	Reconditioning criteria	13
3.1.	Repair	13
3.2.	Cleaning	13
3.3.	Marking.....	14
E.	Conformity to environmental legislation	14
F.	Quality assurance.....	14
G.	Safe Working Load.....	15
H.	Overview CP1 to CP9	17

Attachments [27]

- Design drawings CP1 to CP9;
- Fastening patterns CP1 to CP9;
- Inspection reports CP1 to CP9.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

A. Supplier registration

Suppliers of CP pallets shall ask PlasticsEurope Services for initial registration. Candidates for registration will receive a questionnaire to be filled in. After completion of the administrative filling, the production site will be subject to an initial inspection. The registration costs are 1.250 EUR to be paid in advance charged by PlasticsEurope Services.

The supplier code that PlasticsEurope will adjudge is unique per production site and shall be used for the marking of all newly manufactured CP pallets.

Registered suppliers are committed to respect the manufacturing and reconditioning specifications and to comply with the collection conditions of used CP's [see relevant chapters about the manufacturing & reconditioning specifications and about the collection of used CP's hereafter].

PlasticsEurope Services wants to improve the quality monitoring of the CP pallets to avoid issues related to CP pallets used on the market, like fake pallets, pallets made with low quality materials or pallets not respecting the strict production parameters included in the present guidelines. This situation is creating issues and risks for the users of pallets and also distortion of competition on the market.

Therefore, periodic inspections of the CP pallets production facilities are put in place. The inspections are performed by a professional inspection company.

To also better protect the CP pallets against unfair competition, CP pallets producers have to insert on the right block of each produced CP pallet a the "Certipal" trademark. All contribution for the use of the Certipal trademark and inspections are collected by Certipal Comply based on a new license agreement via: info@certipal.org.

PlasticsEurope Services and its sub-contractors are only in charge of the administration of the CP system. Given this limited role, PlasticsEurope Services cannot be held responsible for any problems or liabilities, which may result from the use of the supplier code.

B. Manufacturing specification

1. Scope

This part of the standard specifies the manufacturing of nine four-way pallets – five skid pallets and four full perimeter base pallets.

They have been designed taking into account the specific requirements of commonly used packages in the chemical industry. Some examples of applied pallet loads are mentioned in table 1.

CP-design	Pallet dimensions	Examples of applied pallet loads
1	1000 × 1200 mm	Sacks, cardboard boxes, Flexible Intermediate Bulk Containers
2	800 × 1200 mm	Cardboard boxes, fibre drums, cans
3	1140 × 1140 mm	Drums, Flexible Intermediate Bulk Containers, octabins
4	1100 × 1300 mm	Sacks
5	760 × 1140 mm	Cardboard boxes
6	1200 × 1000 mm	Sacks
7	1300 × 1100 mm	Sacks
8	1140 × 1140 mm	Octabins with bottom discharge facility
9	1140 × 1140 mm	Drums, Flexible Intermediate Bulk Containers, octabins

Table 1

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

2. Normative references

This specification is based on following international standards:

EN 717-1	2004	Wood based panels – Determination of formaldehyde release – Part 1: Formaldehyde emission by chamber method.
EN 844-6	1997	Round and sawn timber – Terminology – Part 6: Terms relating to dimensions of sawn timber.
EN 844-7	1997	Round and sawn timber – Terminology – Part 7: Terms relating to anatomical structure of timber.
EN 844-8	1997	Round and sawn timber – Terminology – Part 8: Terms relating to features of round timber.
EN 844-9	1997	Round and sawn timber – Terminology – Part 9: Terms relating to features of sawn timber.
EN 844-10	1998	Round and sawn timber – Terminology – Part 10: Terms relating to stain and fungal attack.
EN 1087-1	1995	Particleboards – Determination of moisture resistance – Part 1: Boil test.
EN 1310	1997	Round and sawn timber – Measurement of features.
EN 12246	1999	Quality classification of timber used in pallets and packaging.
ISO 445	2013	Pallets for materials handling – Vocabulary.
ISO 13061-1	2014	Wood – Determination of moisture content for physical and mechanical tests.
ISO 13061-3	2014	Wood – Determination of ultimate strength in static bending.
ISO 6780	2003	General-purpose flat pallets for through transit of goods - Principal dimensions and tolerances.
ISO 8611-1	2011	General purpose flat pallets for through transit of goods – Test methods.
ISPM 15	2009	International Standards for Phytosanitary Measures - Revision

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

3. Construction

3.1. Materials requirements

3.1.1. Sawn timber

3.1.1.1. Wood species

CP's shall be constructed from wood species listed in tables 2 & 3¹.

European grown conifers	Botanical name
Douglas fir	Pseudotsuga ssp.
Fir	Abies ssp.
Larch	Larix ssp.
Pine	Pinus ssp.
Redwood	Pinus sylvestris
Spruce	Picea ssp.

Table 2

European grown deciduous woods	Botanical name
Acacia	Robinia ssp.
Alder ²	Alnus ssp.
Ash	Faxinus excelsior
Beech	Fagus sylvatica
Birch	Betula ssp.
Chestnut [-Horse]	Aesculus hippocastanum
Elm	Ulmus ssp.
Maple	Acer ssp.
Oak	Quercus ssp.
Plane	Platanus ssp.
Poplar ³	Populus ssp.

Table 3

Other species or species grown elsewhere with an ultimate strength in static bending of at least 42 N/mm², measured on samples with a moisture content of 20 % and in accordance with ISO 3133, may be used.

3.1.1.2. Quality

The timber quality⁴ shall conform to the following criteria:

- Bark & bark pockets are not permitted;
- Sound sapwood is permitted;
- Wane [measured according to EN 1310, clause 4.8]:
 - Is only permitted at the underside of intermediate deck boards up to $\frac{1}{3}$ of the thickness of the board;
 - Is not permitted at other components.

¹ The use of weak species affects the Safe Working Load of the pallet. For safety reasons, the respect of the specified species is critical.

² May only be used for deck boards and blocks.

³ May only be used for deck boards and blocks.

⁴ Poor timber quality affects the Safe Working Load of the pallet. For safety reasons, the respect of the quality criteria is critical.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

- Knots [measured according to EN 1310, clause 4.1.2]:
 - Inter-grown or dead knots < 30 mm are permitted;
 - Loose knots & unsound knots < 20 mm are permitted;
 - Branched knots are not permitted.
- Fissures [measured according to EN 1310, clause 4.9]:
 - Splits from one surface to the other in boards or blocks are not permitted;
 - Drying checks are permitted.
- Grain:
 - Significant slope of grain or spiral grain is not permitted.
- Preservatives:
 - No chemical treatment is permitted.
- Deterioration:
 - Mould⁵ or rot⁶ are not permitted;
 - Active insect infestation is not permitted;
 - Some blue stain⁷ is permitted.

3.1.1.3. Moisture content

The maximum moisture content⁸ of timber is not defined in this document. CP's may be constructed from green timber. If not specified differently by the user, CP's will be supplied without any drying. The moisture content of green timber is normally higher than 30 %.

3.1.1.4. Packaging issues related to wet timber [informative]

For some packages such as, cardboard boxes and paper sacks and for hygroscope products the moisture content of green timber might be unacceptable.

If only migration of moisture from the timber into the packaging material has to be avoided, limitation of the moisture content of the deck boards is in most cases sufficient.

A good practice is, as they are drying slower than intermediate deck boards, to check the moisture content of the lead & central deck boards.

An achievable value in Middle-European climate, avoiding artificial drying is 25 % moisture content.

If on the other hand the presence of moisture is very critical, the moisture content of all timber components shall be checked.

In that case values of moisture content below 20 % are required and in most seasons pallets have to be dried artificially.

⁵ Mould is an infestation of timber by fungi that penetrate into wet wood.

⁶ Rot is an infestation by fungi or other micro-organisms, showing a brown coloured and cubic-segmented structure or zones composed of soft decomposed fibres without strength. Rot affects the Safe Working Load of the pallet.

⁷ Blue stain is a blue to black discoloration, caused by fungi, of the sapwood of conifers and some deciduous woods. As chemical treatment is not permitted, blue stain cannot be completely avoided in certain seasons, but does not affect the strength of the timber.

⁸ Moisture content can be determined using portable battery operated moisture meters.

CP**CHEMICAL INDUSTRY PALLETS**

July 2017

Edition: 7

3.1.2. Particleboard blocks [optional]

High density, moisture resistant particleboard conforming to the following criteria may be used for blocks:

- Made exclusively from timber particles without any wood preservative;
- The mean weight per unit volume shall be minimum 0,580 g/cm³;
- The moisture content shall be between 7 and 13 %;
- The material shall produce a formaldehyde emission less than 0,1 ml per cubic meter of air, when determined in accordance with ENV 717-1;
- The bonding shall ensure, that the material is permanently bonded; the efficiency of the bonding process shall be determined in accordance with EN 1087-1;
- Retention of material strength, absence of splits, no loss of cohesion after test cycle in accordance with EN 1087-1 involving:
 - A two-hour immersion in water at 100 °C under ambient pressure;
 - Two hours drying in the oven at 65 °C [\pm 3 %].

3.1.3. Plastic blocks [optional]

Plastic conforming to the following criteria may be used for blocks:

- Composition:
 - Made of post-consumer mixed plastics;
 - Minimum density \geq 0,800 g/cm³;
 - Specific shares to be met [in weight percentages]:
 - Polyolefin > 50 %;
 - Paper, wood flour, aluminium film < 5%;
 - Glass, stones, metals < 0,05 %.
- Design:
 - Square profile; round vertical corners up to a radius of 5 mm are permitted;
 - Vacuoles < 5 mm are permitted;
 - Concavity or convexity of the nailing surface shall be limited to 1 mm;
 - Hollow spaces and depressions, if present, shall be positioned at a minimum distance of 10 mm from the nailing position.
- The minimum weight shall conform to the values shown in table 4;

Block dimension	Minimum weight
135 mm × 80 mm × 80 mm	0,550 kg
120 mm × 80 mm × 80 mm	0,480 kg
100 mm × 80 mm × 80 mm	0,400 kg

Table 4

- The colour shall be dark grey to black;
- Unpleasant smelling is not permitted.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

3.1.4. Fasteners

Depending on their position, different types of fasteners are needed to manufacture CP's [see also attached fastening patterns CP1 to CP9].

Nails shall conform to the criteria of table 5.

Nails	Type N1	Type N2	Type N3
Shank	Square twisted, spiral rolled or annular ring rolled	Plain	Square twisted, spiral rolled or annular ring rolled
Wire Ø	Minimum 3,4 mm	Minimum 2,5 mm	Minimum 3,4 mm
Length	Minimum 90 mm	Minimum 45 mm	Minimum 70 mm
Head Ø	Minimum 8,0 mm	Minimum 6,0 mm	Minimum 8,0 mm
Point	Diamond or chisel	Diamond or diamond offset ⁹	Diamond or chisel
Material	Steel	Steel	Steel
Tensile strength	Minimum 700 N/mm ²	Minimum 800 N/mm ²	Minimum 650 N/mm ²

Table 5

Optionally also staples may be used. They shall conform to the criteria of table 6.

Staples	Type N1	Type N2	Type N3
Wire Ø	Minimum 2,5 mm	Minimum 1,8 mm	Minimum 2,5 mm
Length	Minimum 2 × 90 mm	Minimum 2 × 45 mm	Minimum 2 × 70 mm
Material	Steel	Steel	Steel
Tensile strength	Minimum 650 N/mm ²	Minimum 750 N/mm ²	Minimum 600 N/mm ²

Table 6

3.2. Dimensions

3.2.1. Pallet dimensions & permitted deviations

Pallet dimensions and permitted deviations shall be as shown in the attached design drawings CP1 - 9. The permitted length & width deviation is ± 3 mm. The permitted height deviation is + 5 / - 2 mm.

Pallets shall be square. The difference between diagonals shall not exceed 10 mm.

3.2.2. Permitted deviations of component parts made of sawn green timber

The permitted deviations of the component parts are mentioned in table 7 [see also attached design drawings CP1 to CP9].

Component	Dimension	Permitted deviations
Board	Length	+ 0 / - 3 mm
	Width	+ 3 / - 0 mm
	Thickness	+ 2 / - 0 mm
Block	Length	+ 2 / - 2 mm
	Width	+ 2 / - 2 mm
	Height	+ 2 / - 2 mm

Table 7

⁹ Diamond points shall be used if the nailing bar is movable, diamond offset points if the nailing bar is fixed.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

3.2.3. Permitted timber dimensions considering moisture content

The nominal dimensions & permitted deviations of the components in the attached design drawings are dimensions, which are intended to be achieved after the sawing process of green timber. These are the references for the pallet manufacturer when ordering timber.

The minimum dimensions¹⁰ of table 8, which take into account the shrinkage of timber when drying shall be respected.

Measure	Nominal dimension	Minimum dimension moisture content < 30 %
Board thickness	18 mm	17 mm
	22 mm	21 mm
	36 mm	34 mm
Board width	75 mm	71 mm
	80 mm	76 mm
	100 mm	95 mm
	120 mm	114 mm
	125 mm	119 mm
	135 mm	128 mm
Block height & width	80 mm	74 mm

Table 8

3.3. Manufacturing requirements

3.3.1. Component parts

All boards and natural timber blocks shall be of one piece.

Blocks shall be of natural timber, particleboard [see clause 3.1.2. Particleboard blocks] or plastic [see clause 3.1.3. Plastic blocks].

3.3.2. Assembly

The position of the components shall conform to the attached design drawings. The permitted deviations in the assembled pallet are +3 and -3 mm.

Unless specified differently in the attached design drawings, the top deck boards shall be equally spaced.

The fixation of natural timber blocks shall conform to the indications of table 9 & 10:

- The fixation of (=) indicated species shall be in parallel to the direction of the wood fibres;
- The fixation of (#) indicated species shall be square to the direction of the wood fibres.

European grown conifers	Botanical name	Fixation of blocks
Douglas fir	Pseudotsuga ssp.	#
Fir	Abies ssp.	#
Larch	Larix ssp.	#
Pine	Pinus ssp.	#
Redwood	Pinus sylvestris	#
Spruce	Picea ssp.	#

Table 9

¹⁰ For safety reasons the respect of minimum dimensions is critical.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

European grown deciduous woods	Botanical name	Fixation of blocks
Acacia	Robinia ssp.	#
Alder ¹¹	Alnus ssp.	#
Ash	Faxinus excelsior	#
Beech	Fagus sylvatica	= or #
Birch	Betula ssp.	= or #
Chestnut [-Horse]	Aesculus hippocastanum	= or #
Elm	Ulmus ssp.	#
Maple	Acer ssp.	= or #
Oak	Quercus ssp.	= or #
Plane	Platanus ssp.	#
Poplar ¹²	Populus ssp.	#

Table 10

Missing components are not permitted.

3.3.3. Joints

All fasteners shall be driven in vertically. They shall not be driven in the same wood fibre. The number, the type and the positioning of fasteners shall conform to the attached fastening patterns, both for nails and staples [one nail = one staple].

Fasteners shall not protrude above the surface of the board. Nail heads shall be countersunk between 2 and 4 mm below the surface of the board.

Points of fasteners type N2 protruding below the top or bottom stringer boards shall be bent back. Fasteners shall not pierce the sides of blocks¹³.

No splits resulting from assembling shall be visible on boards or blocks.

3.3.4. Bottom board chamfer [optional]

Bottom boards may be chamfered as shown in figure 1.

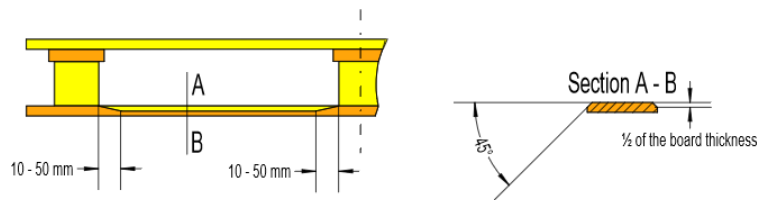


Figure 1

¹¹ May only be used for deck boards and blocks.

¹² May only be used for deck boards and blocks.

¹³ Protruding or piercing nails are dangerous. For safety reasons, the respect of the specified requirements is critical.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

3.3.5. Finishing

All timber components shall be sawn squarely and have a clean cut.
The outer surfaces of the deck and bottom boards shall not be planed.

Except for CP5, the four corners of the pallets shall be chamfered as shown in the attached design drawings.

Pallets shall be clean.

3.3.6. Marking

CP's shall be marked on the outer side of the blocks as shown in figure 2.
Markings shall be clearly legible. Only following techniques shall be used:

- Natural timber and particleboard blocks, by hot strong burning;
- Plastic blocks, by hot strong burning or by hot film stamping in white.

As the CP Pallets producers should follow the International Standard for Phytosanitary Measures (ISPM), number 15 rules, we now introduce in this edition the obligation to put on the left block the ISPM 15 mark of the CP pallets producer.

To improve the quality monitoring of the CP pallets, we also introduce on the right block the use of the registered trademark "Certipal" that is associated with regular plant inspections organised by a professional inspection company.

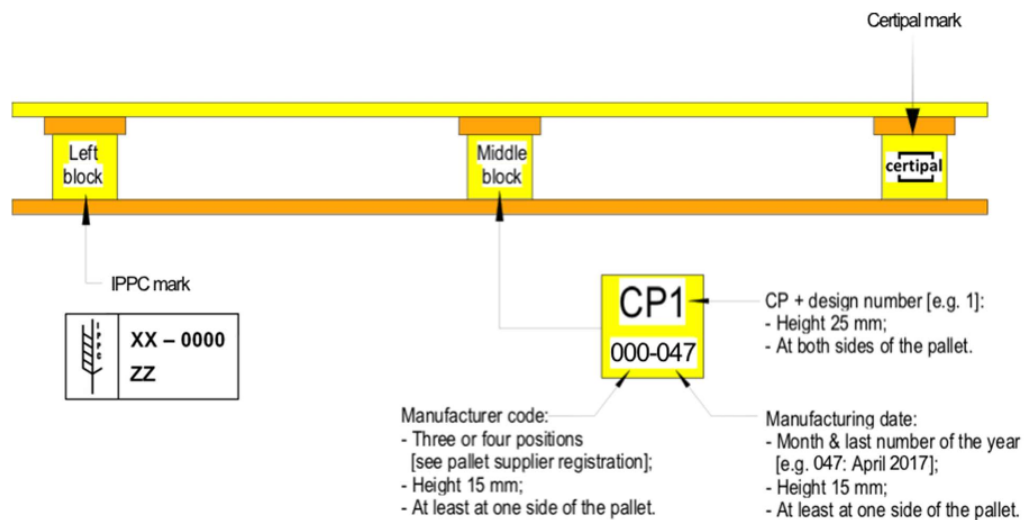


Figure 2

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

C. Collection of used CP's

When requested, the registered CP supplier [see chapter A. Pallet supplier registration] shall offer to owners of used CP's the free collection of pallets up to at least 50 km from his facilities and shall respect the lead times of table 11.

Number of pallets	Maximum collection lead time
> 400	2 weeks
100 – 400	4 weeks
20 - 100	3 months

Table 11

No free collection has to be offered if:

- More than 10 % of the pallets have unacceptable deficiencies [see chapter D. Reconditioning specification];
- Less than 20 pallets are offered; they shall be accepted without costs when delivered to the registered supplier or collected after payment of transport costs.

No collection shall be offered for pallets manufactured without respect of the manufacturing specifications [poor timber quality or thickness, missing manufacturing markings, etc.] or for pallets contaminated with chemical products.

D. Reconditioning specification

1. Scope

This part of the standard defines the unacceptable deficiencies of used CP's, and specifies the reconditioning criteria.

2. Unacceptable deficiencies

The following conditions make CP's unacceptable for re-use¹⁴ and acceptance for reconditioning is limited to 10 % of the total amount of offered pallets:

- Missing or broken components;
- Component damage such as:
 - Missing wood on boards > ¼ of the width of the board or making a fastener shank visible;
 - Splits on boards > ½ of the width of the board;
 - Warped boards > ½ of the thickness of the board;
 - Missing wood on blocks, making a fastener shank visible;
 - Splits on blocks.
- Loose components or fasteners;
- Twisted blocks;
- Protruding nail heads;
- Pallets with mould or rot;
- Dirty or contaminated pallets;
- Pallets with materials or components that have been previously incorrectly applied.

Minor damages as a result of normal use and discoloration due to the weathering are permitted.

Pallets, which are unacceptable for re-use, shall either be reconditioned or disposed of properly.

¹⁴ Unacceptable deficiencies make the pallet unsafe.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

3. Reconditioning criteria

3.1. Repair

The acceptance of pallets for re-use is strongly influenced by the quality of the repair¹⁵.

Damaged components shall be removed and replaced.

The replacing components shall be from either new timber or re-used CP-timber.

New components or re-used CP-components and fasteners shall conform to the manufacturing specification [see clause 3.1. Materials requirements & clause 3.2. Dimensions].

The assembly shall conform to the manufacturing specification [see clause 3.3. Manufacturing requirements].

Loose components, split boards and twisted blocks shall be put back in the original position and fixed. Protruding nail heads shall be hammered flush to the surface of the board.

The number of fasteners per joint and the positioning shall repeat the original pattern [see attached fastening patterns CP1 to CP9].

If extra fasteners have to be used, they shall be positioned never closer than 15 mm either from the end or from the edge of a component.

Collated nails used in pneumatic tools shall meet the criteria of table 12.

Nails	Type N1	Type N2	Type N3
Shank	Square twisted, spiral rolled or annular ring rolled	Annular ring rolled	Square twisted, spiral rolled or annular ring rolled
Wire Ø	Minimum 3,1 mm	Minimum 2,0 mm	Minimum 2,5 mm
Length	Minimum 80 mm	Minimum 35 mm	Minimum 60 mm
Point	Diamond	Diamond or diamond offset	Diamond
Material	Steel	Steel	Steel
Tensile strength	Minimum 700 N/mm ²	Minimum 800 N/mm ²	Minimum 650 N/mm ²

Table 12

3.2. Cleaning

Dirt shall be removed. If any doubt exists as to the nature of the contamination, the pallets shall be disposed of properly.

¹⁵ For safety reasons, the respect of the specified repair criteria is critical.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

3.3. Marking

Reconditioned CP's shall be marked on the outer side of the blocks as shown in figure 3 [see also attached design drawings CP1 to CP 9].

Markings shall be clearly legible. Only following techniques shall be used:

- Natural timber and particle board blocks, by hot strong burning or by ink stamping; paint is not allowed;
- Plastic blocks, by hot strong burning or by hot film stamping in white.

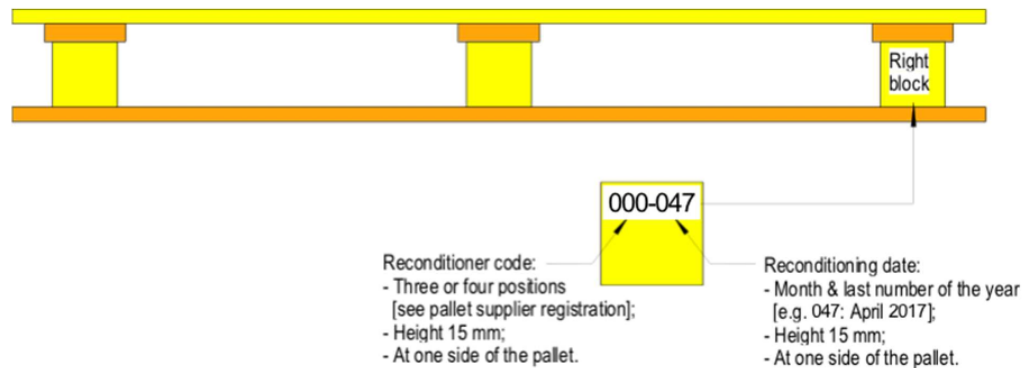


Figure 3

The first reconditioning shall be marked at the top of the block, the second reconditioning below, etc.

E. Conformity to environmental legislation

Both newly manufactured and reconditioned CP's shall conform to the current European Packaging and Packaging Waste Directive, 94/62/EC at the moment.

F. Quality assurance

Suppliers of non-conforming quality can be liable in case of damage or accident.

Visual inspection for quality can be done in accordance with the attached inspection reports.

G. Safe Working Load

Experience has demonstrated that the Safe Working Load of a given pallet is strongly influenced by the type of the applied load.

The effect of different types of load such as, centrally placed loads, interlocked or not-interlocked units, various patterns of sacks, Flexible or Rigid Intermediate Bulk Containers, etc., and the influence of securing or wrapping.

Besides the application of a loaded pallet is important. Pallet racking is considered as the most severe kind of application. The Safe Working Load of racked pallets can be defined by the method¹⁶ described hereafter.

The Safe Working Load defined this way is also valid for less severe kinds of application such as block stacking.

Method to define the Safe Working Load of racked pallets:

- Place 3 CP-replicates with the same applied load on pallet supports, parallel to the direction of the deck boards as shown in figure 4 [this is the weakest direction of all CP-designs];
- Measure the deflection at point A, B and C after 24 hours. In case of packed solids one testing hour is sufficient, as afterwards the deflection will not change significantly.

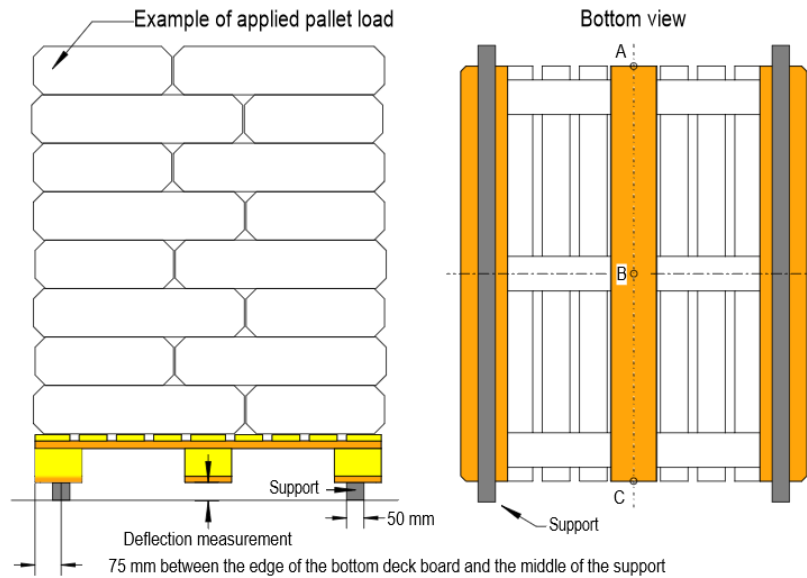


Figure 4

¹⁶ This method is accurate to the best of our knowledge. No liability whatsoever arising from the use of this method can be accepted.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

The average deflection at point A, B & C of each pallet shall be lower than the maximum deflection values shown in table 13. If the average deflection exceeds those values, the Safe Working Load of racked pallets has been exceeded. The applied load has to be reduced and the test shall be repeated with less weight until no exceeding of the maximum deflection is measured.

CP-design	Maximum deflection	Average breaking load
1	12 mm	10,2 kN
2	12 mm	14,8 kN
3	19 mm	9,0 kN
4	14 mm	9,8 kN
5	12 mm	13,5 kN
6	16 mm	18,2 kN
7	17 mm	16,3 kN
8	18 mm	19,6 kN
9	17 mm	15,8 kN


Table 13

The values in table 13 have been defined with the bending test specified in ISO 8611. The maximum deflection corresponds to the value at 50 % of the breaking load, which means the rated load of the pallet with a safety factor of two. The average breaking load has been defined with 5 replicates constructed from a weak wood species but conforming to the specified timber quality with an ultimate strength in static bending of 42 N/mm². The test described here above should be performed with pallets of comparable quality.


Deflection tests are not necessary when the Safe Working Load has already been defined for similar applications.

CP	CHEMICAL INDUSTRY PALLETS	July 2017
		Edition: 7

H. Overview CP1 to CP9

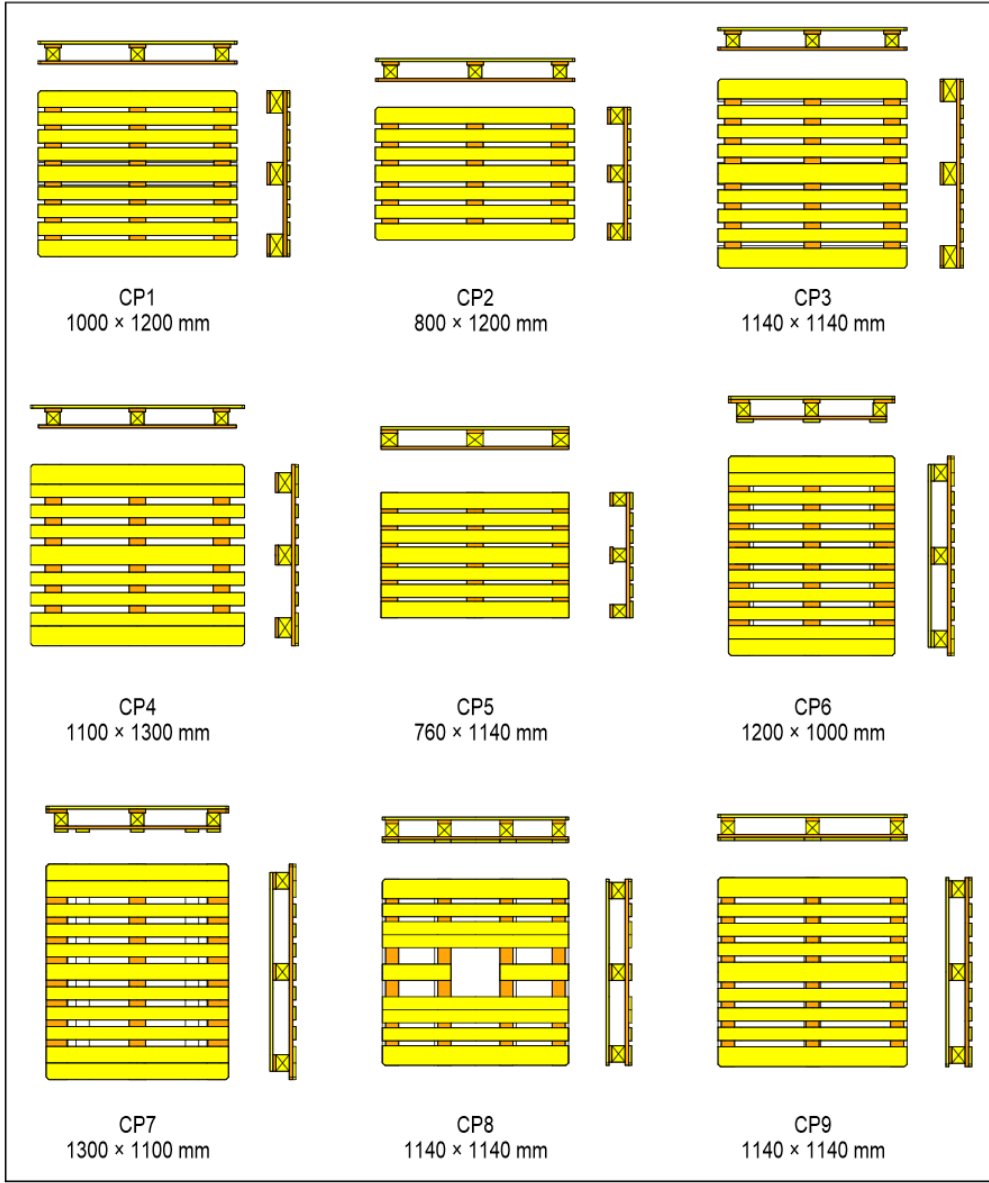


Design drawing

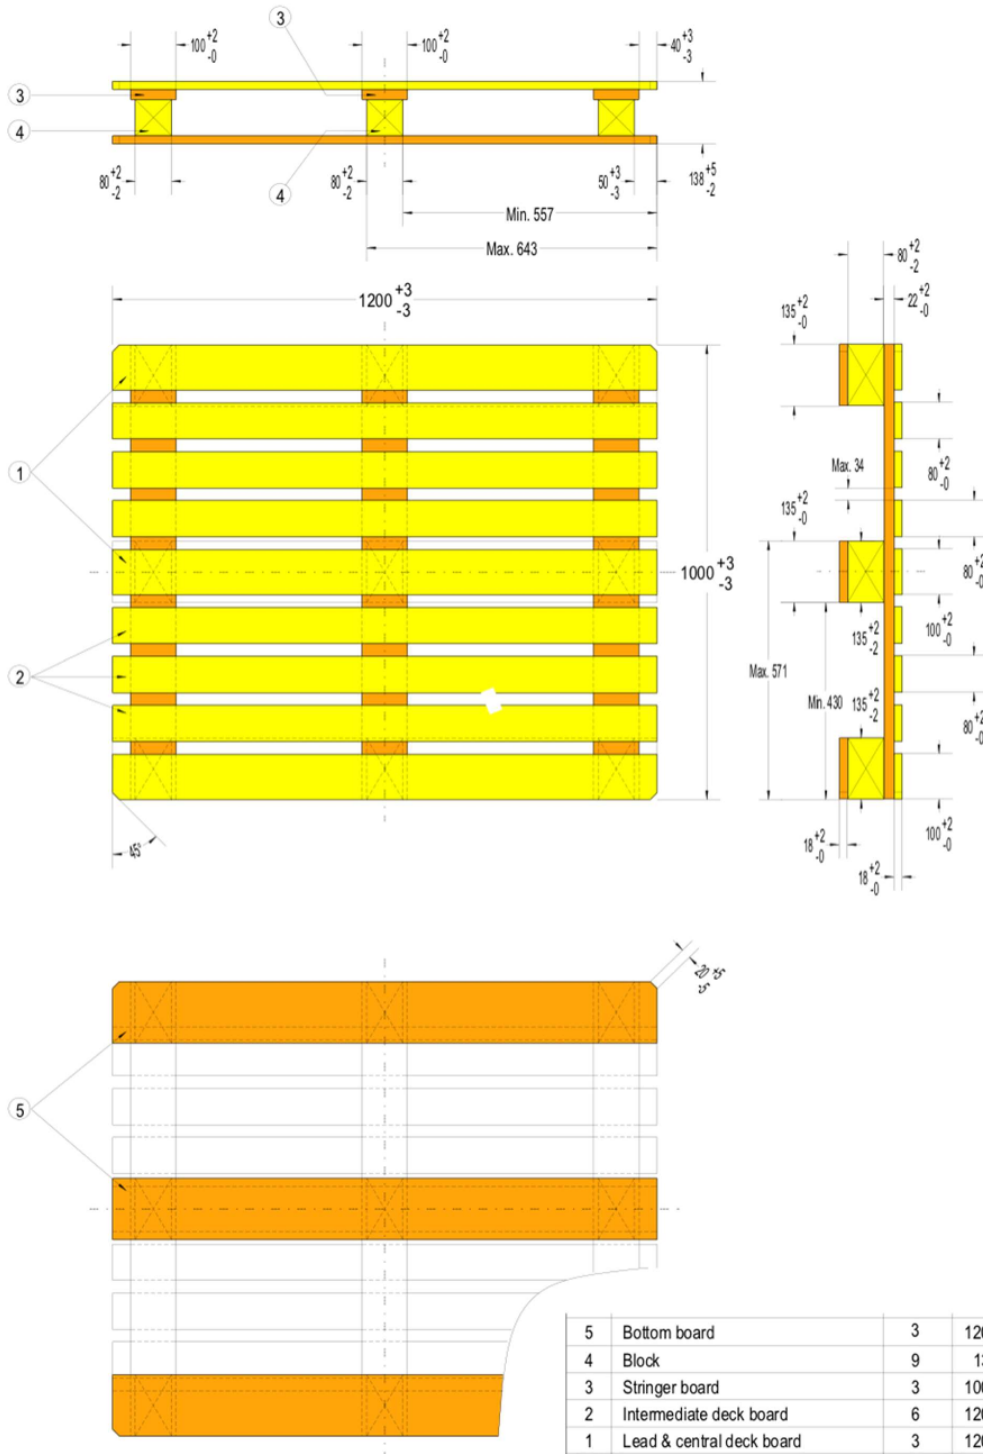

5	Bottom board	3	1200 × 135 × 18
4	Block	9	135 × 80 × 80
3	Stringer board	3	1000 × 100 × 22
2	Intermediate deck board	6	1200 × 80 × 18
1	Lead & central deck board	3	1200 × 100 × 18


Nr.	Denomination	Number	Nominal dimensions
Nominal timber volume: 40,0 dm ³			CP1
Unit of measurement: mm Projection			
Wooden pallet 1000 × 1200 mm			July 2017
			Edition: 7

Fastening pattern

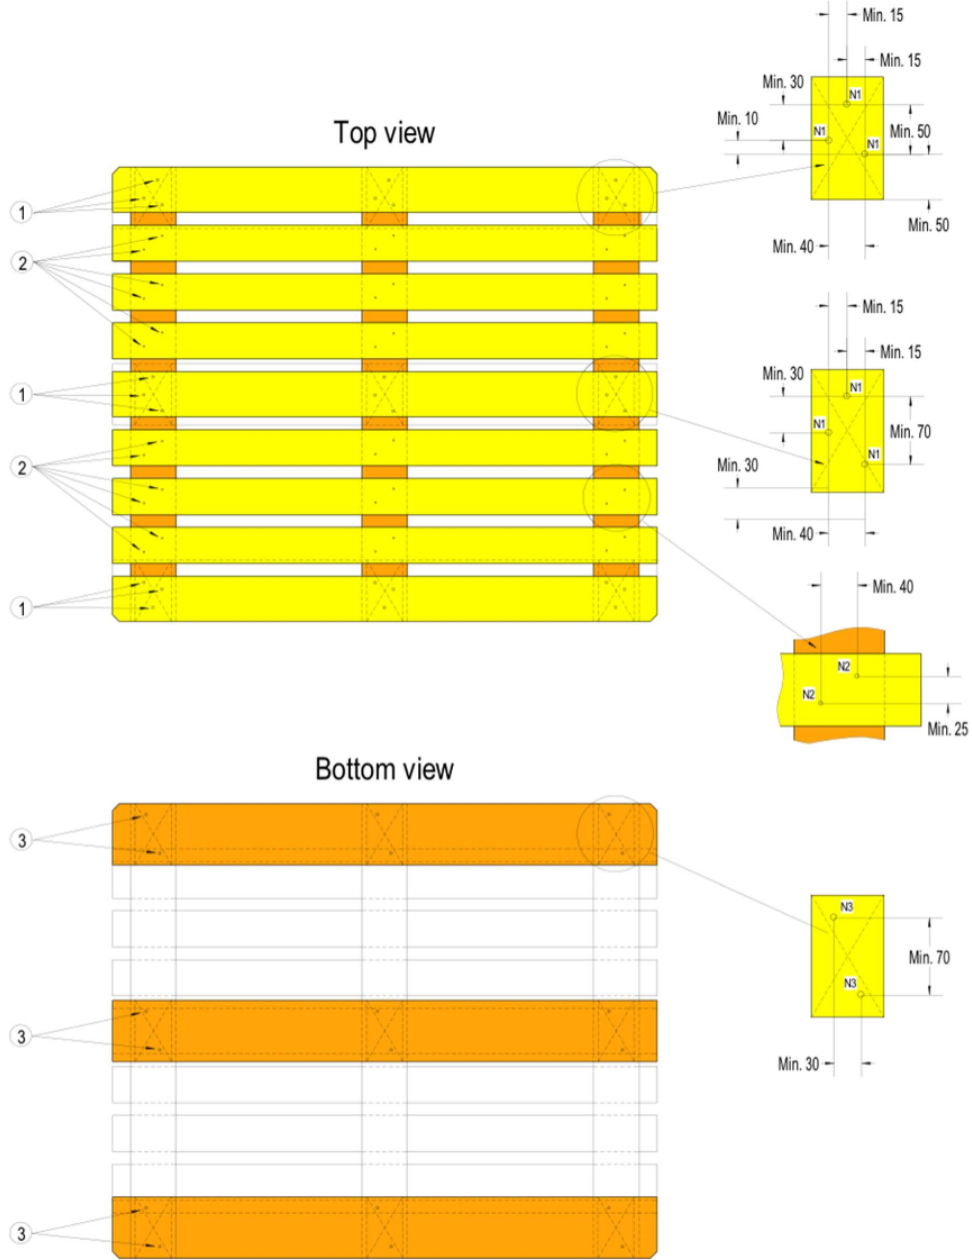

3	Bottom board - block	18 × N3
2	Intermediate deck board - stringer board	36 × N2
1	Lead & central deck board - stringer board - block	27 × N1
Position	Joint	Number
		CP1
Unit of measurement: mm		July 2017
Wooden pallet 1000 × 1200 mm		Edition: 7


Design drawing

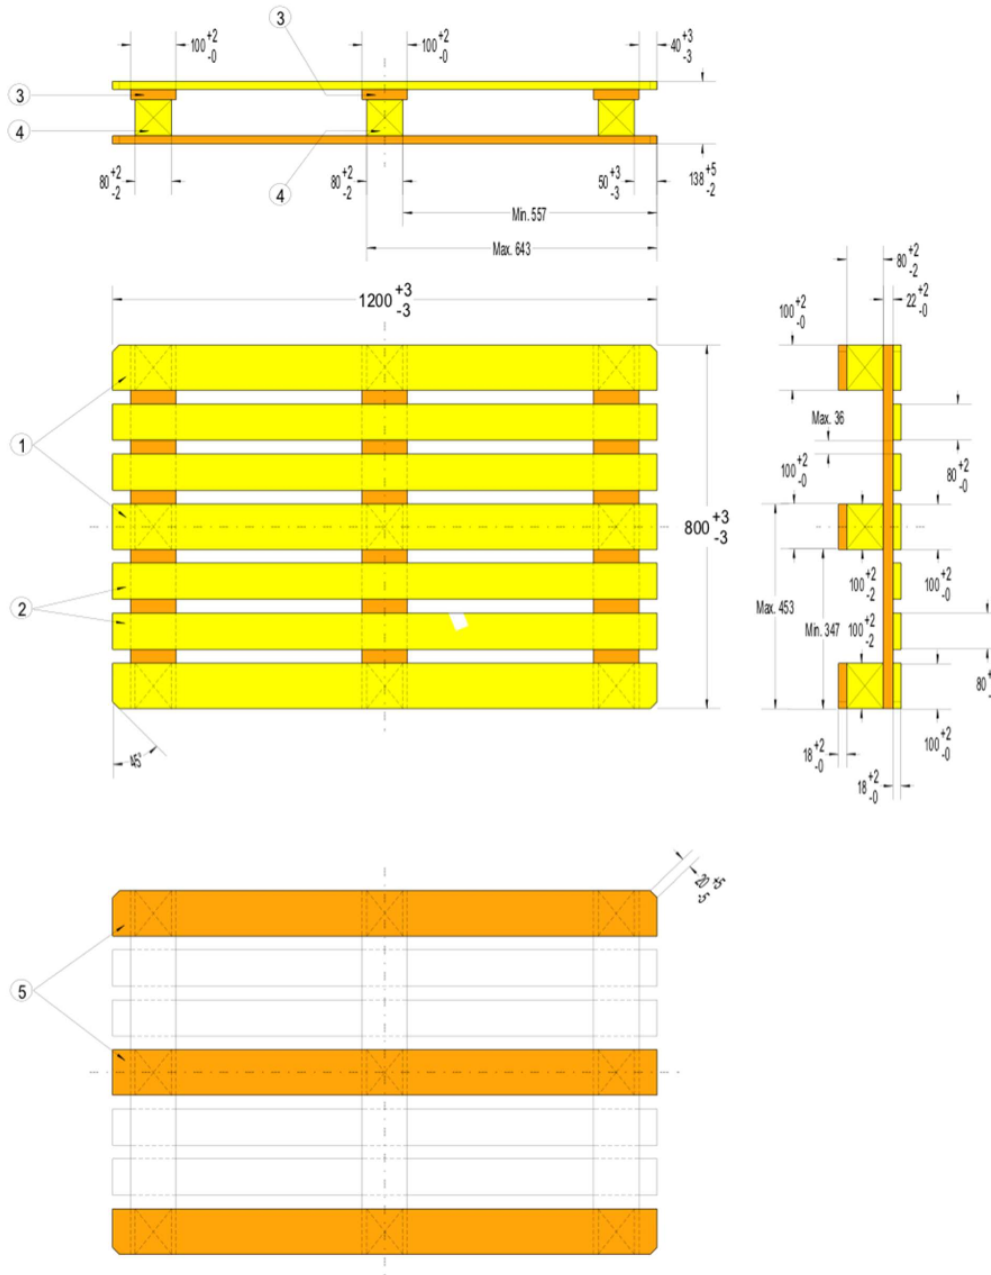

5	Bottom board	3	1200 × 100 × 18
4	Block	9	100 × 80 × 80
3	Stringer board	3	800 × 100 × 22
2	Intermediate deck board	4	1200 × 80 × 18
1	Lead & central deck board	3	1200 × 100 × 18


Nr.	Denomination	Number	Nominal dimensions
Nominal timber volume: 30,9 dm ³			CP2
Unit of measurement: mm Projection			
Wooden pallet 800 × 1200 mm			July 2017
			Edition: 7

Fastening pattern

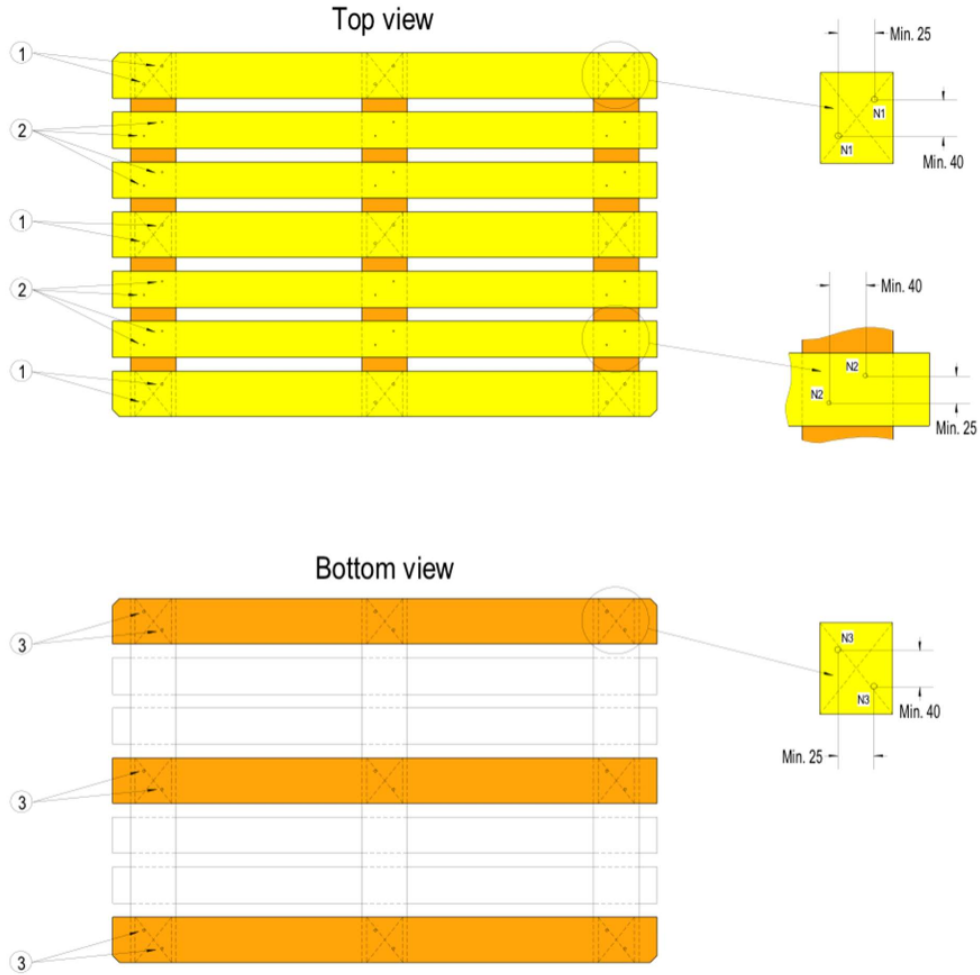


3	Bottom board - block	18 × N3
2	Intermediate deck board - stringer board	24 × N2
1	Lead & central deck board - stringer board - block	18 × N1
Position	Joint	Number
		<h1>CP2</h1>
Unit of measurement: mm		
Wooden pallet 800 × 1200 mm		
		July 2017
		Edition: 7

Design drawing

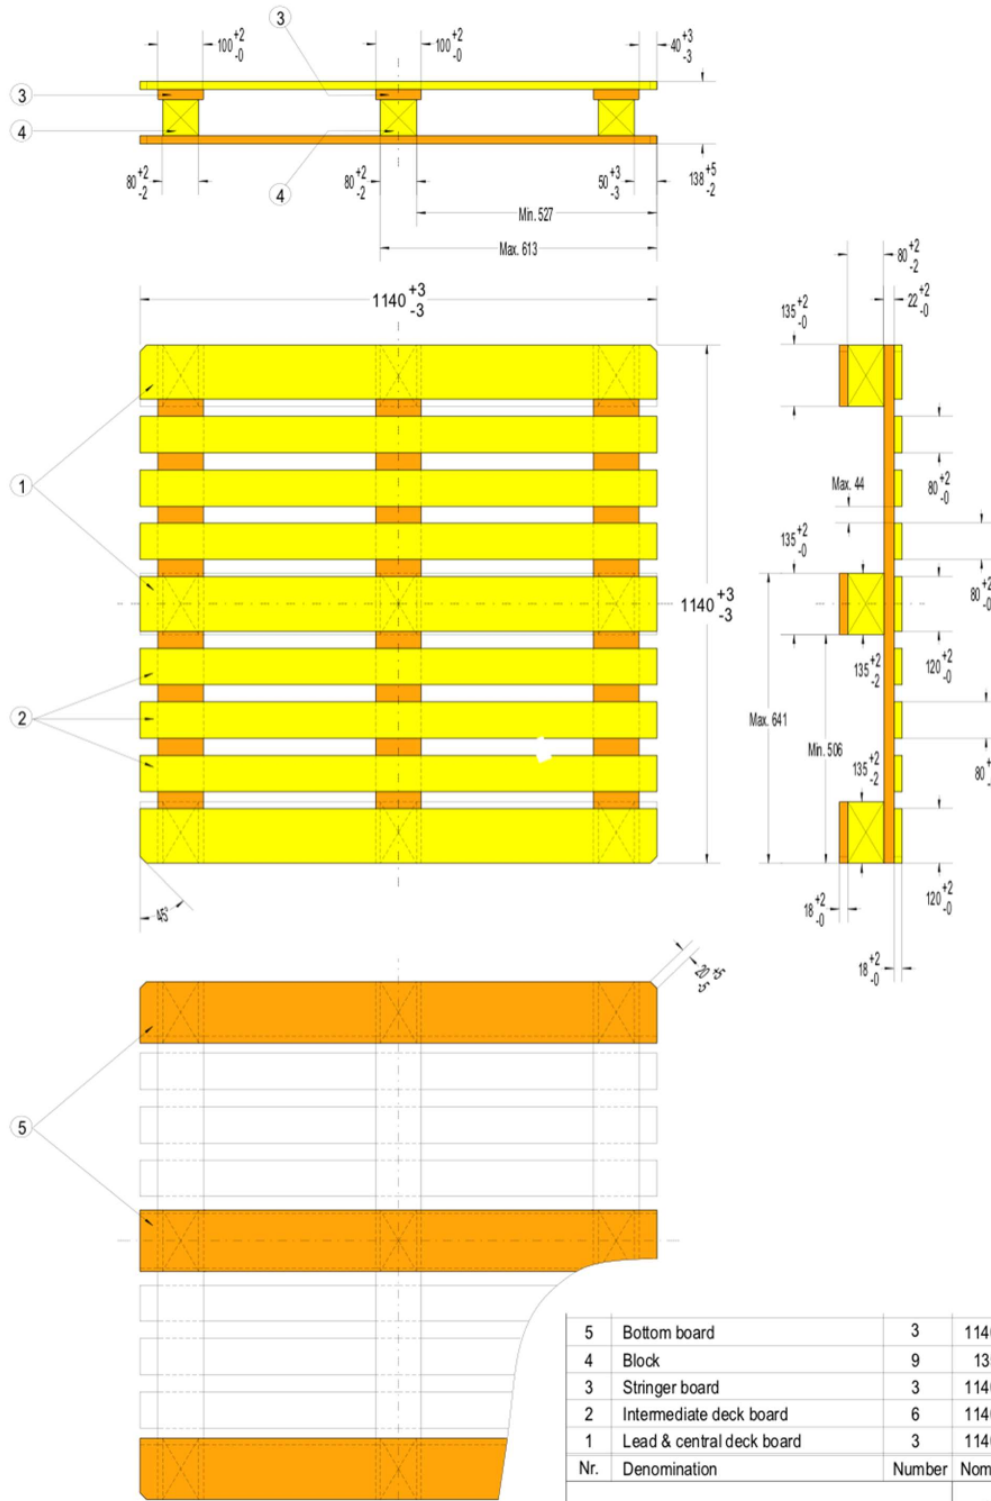

5	Bottom board	3	1140 × 135 × 18
4	Block	9	135 × 80 × 80
3	Stringer board	3	1140 × 100 × 22
2	Intermediate deck board	6	1140 × 80 × 18
1	Lead & central deck board	3	1140 × 120 × 18
Nr.	Denomination	Number	Nominal dimensions
Nominal timber volume: 40,8 dm ³			CP3
Unit of measurement: mm		Projection	
Wooden pallet 1140 × 1140 mm			July 2017
			Edition: 7


Fastening pattern

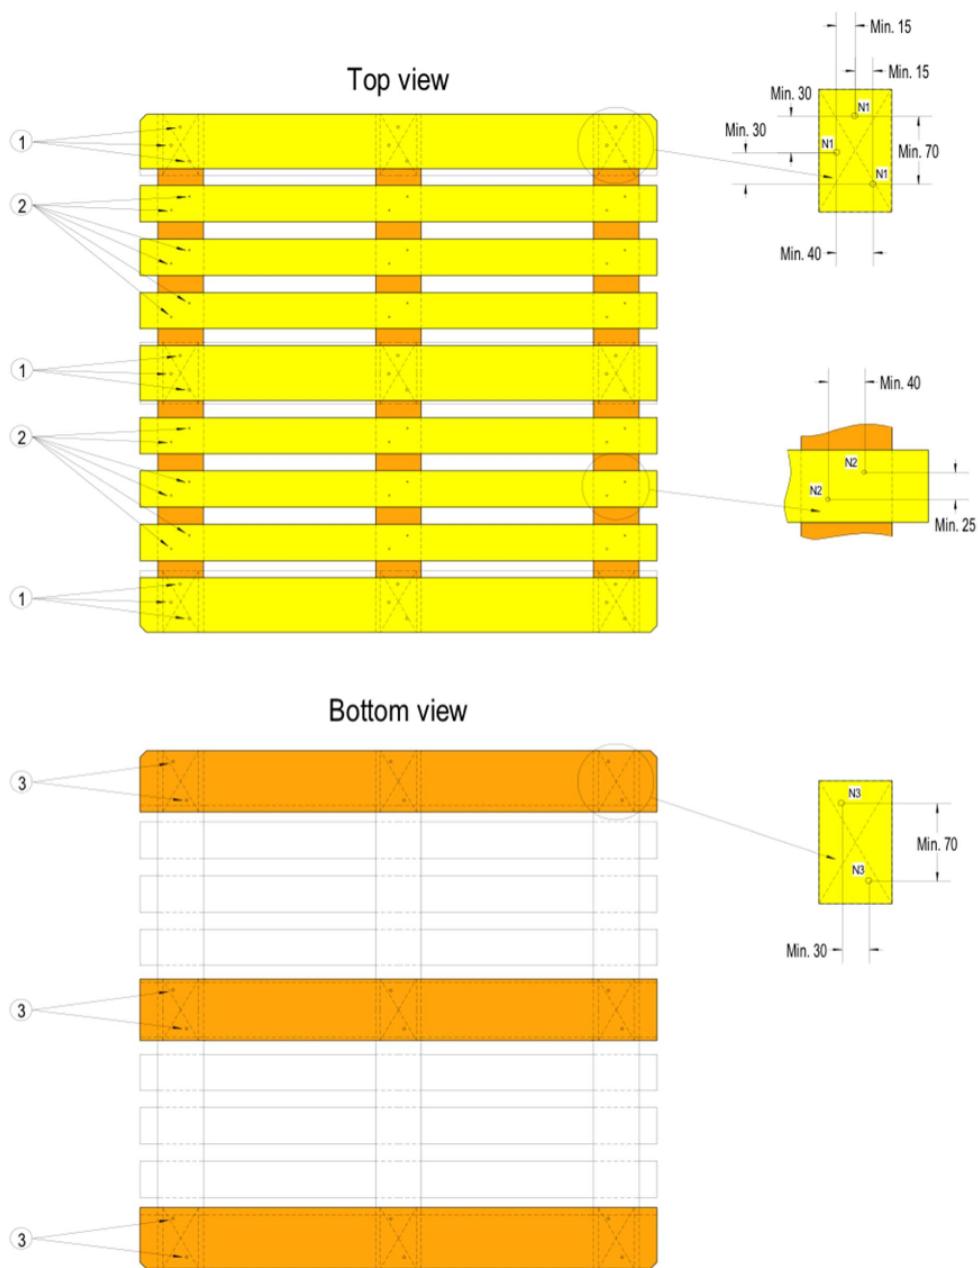

3	Bottom board - block	18 × N3
2	Intermediate deck board - stringer board	36 × N2
1	Lead & central deck board - stringer board - block	27 × N1
Position	Joint	Number
		<h1>CP3</h1>
Unit of measurement: mm		
Wooden pallet 1140 × 1140 mm		
		July 2017
		Edition: 7

Design drawing

Attention, the position of the deck boards has been changed!

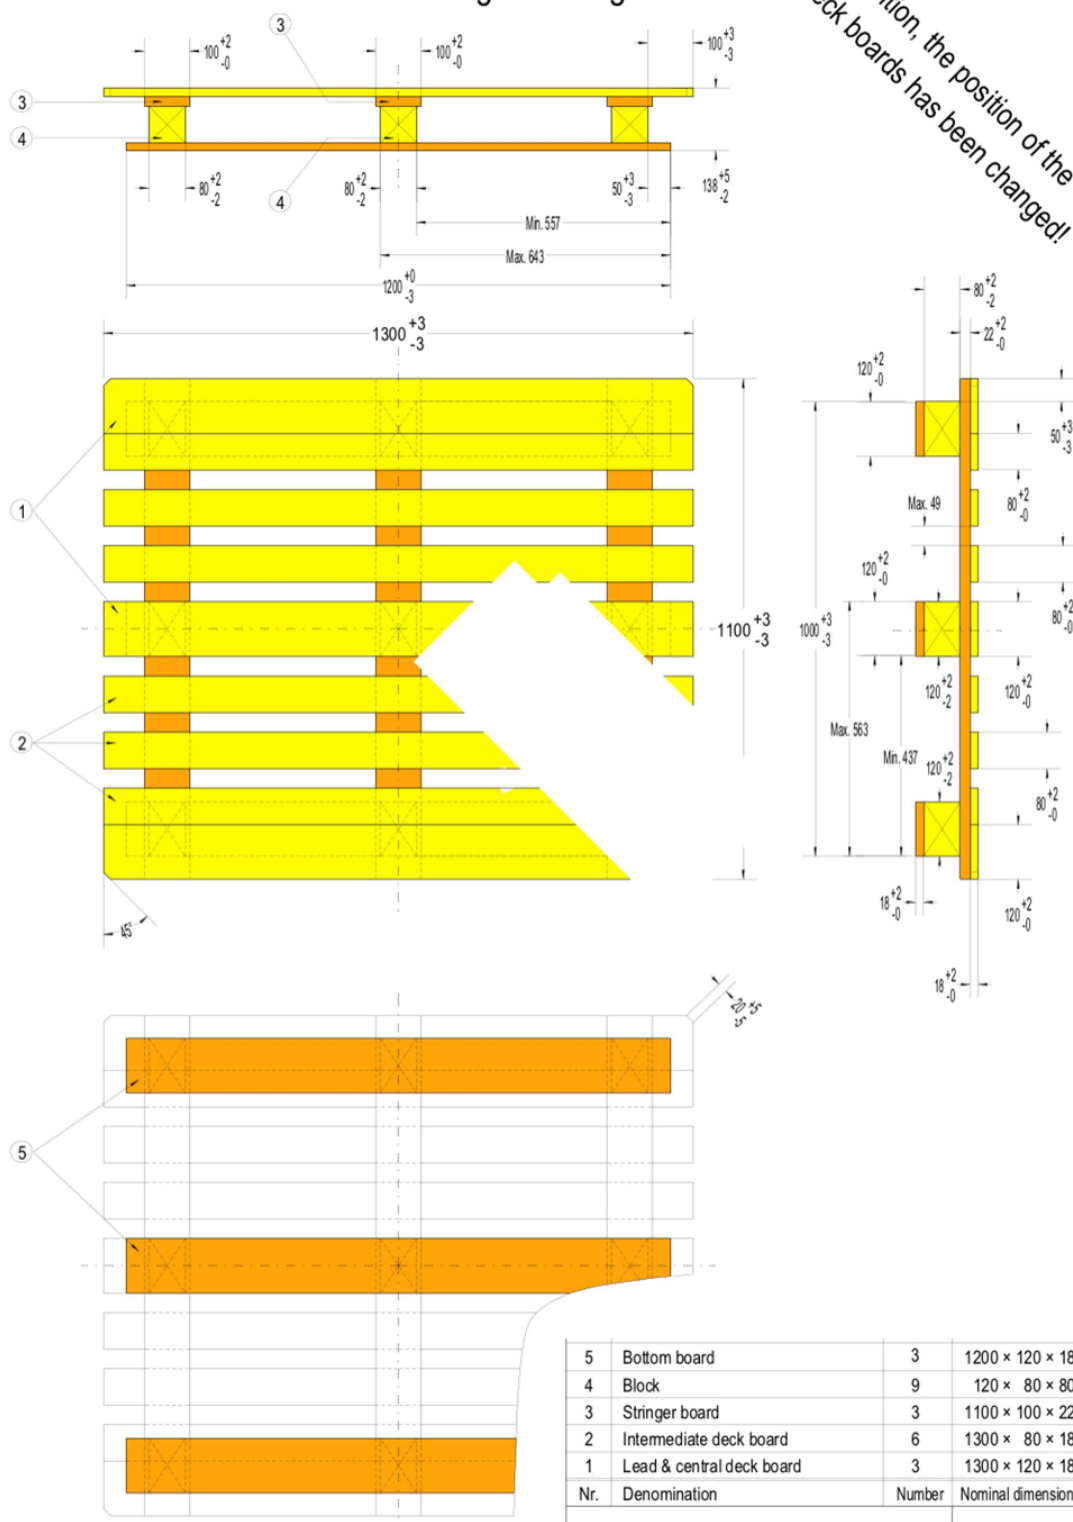

5	Bottom board	3	1200 × 120 × 18
4	Block	9	120 × 80 × 80
3	Stringer board	3	1100 × 100 × 22
2	Intermediate deck board	6	1300 × 80 × 18
1	Lead & central deck board	3	1300 × 120 × 18
Nr.	Denomination	Number	Nominal dimensions

Nominal timber volume: 41,6 dm³
 Unit of measurement: mm Projection


CP4

July 2017
Edition: 7


Wooden pallet 1100 × 1300 mm

Fastening pattern

Top view

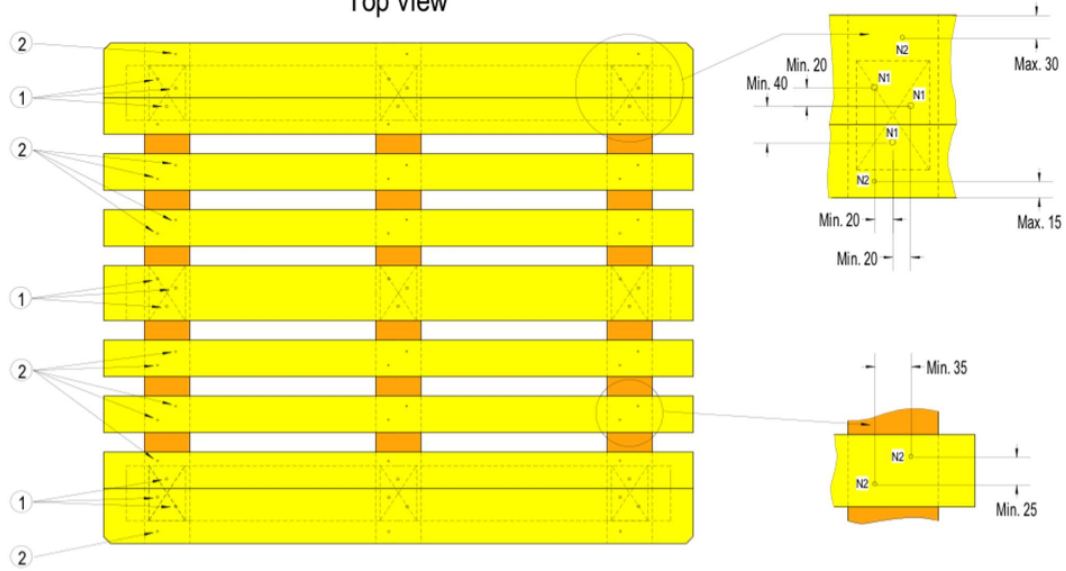


Bottom view

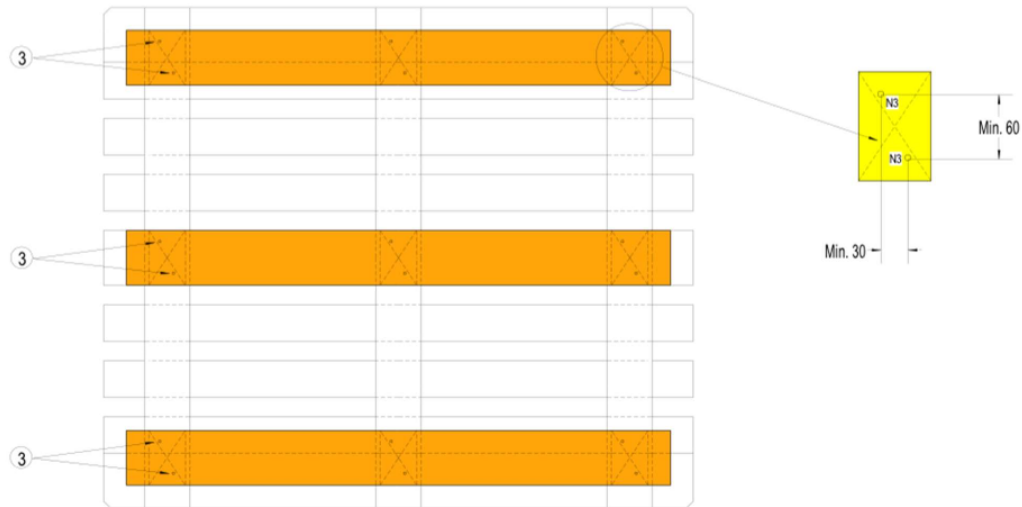

3	Bottom board - block	18 × N3
2	Deck board - stringer board	42 × N2
1	Lead & central deck board - stringer board - block	27 × N1
Position	Joint	Number
		CP4
Unit of measurement: mm		
Wooden pallet 1100 × 1300 mm		
		July 2017
		Edition: 7


Design drawing

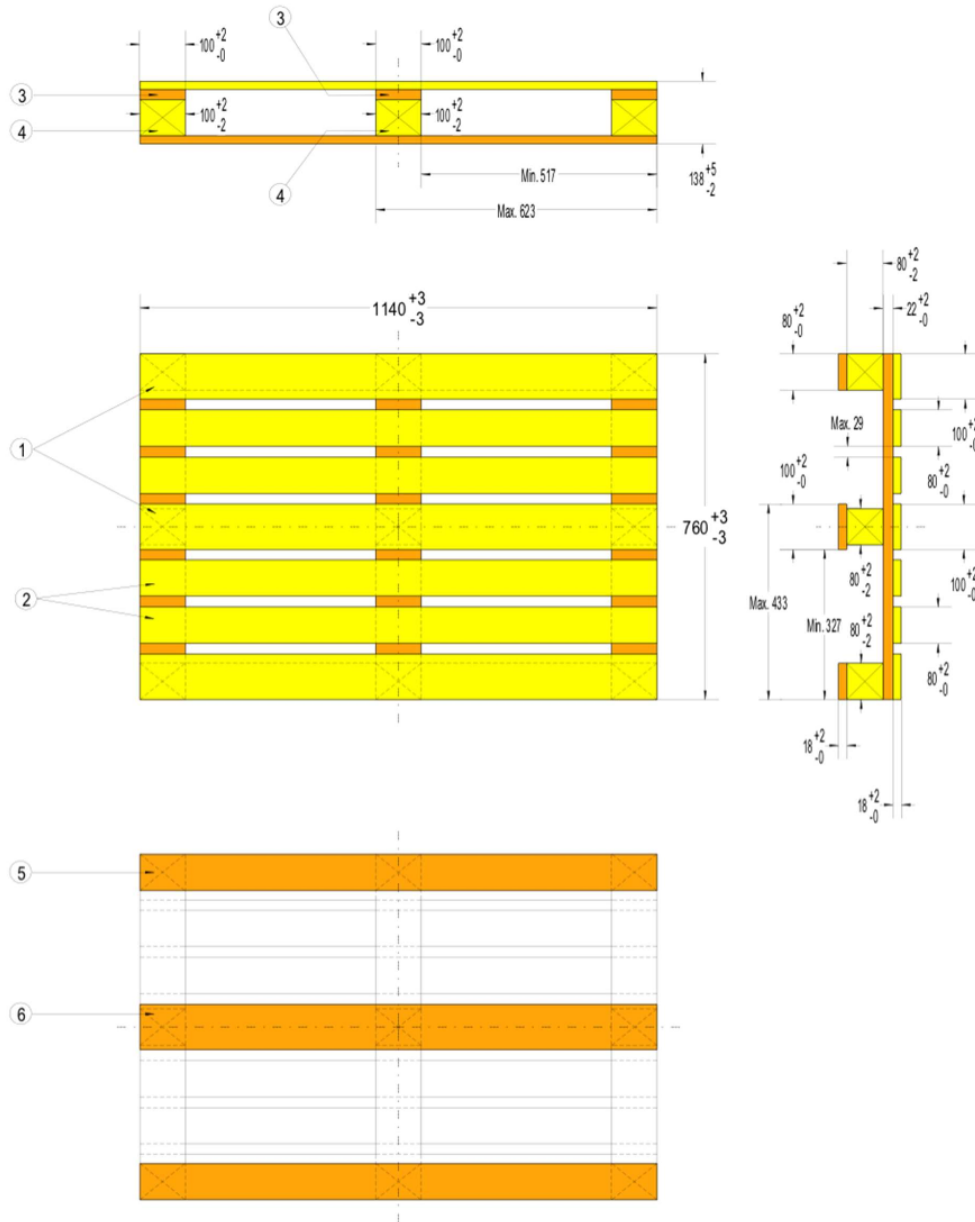

6	Central bottom board	1	1140 × 100 × 18
5	Lead bottom board	2	1140 × 80 × 18
4	Block	9	100 × 80 × 80
3	Stringer board	3	760 × 100 × 22
2	Intermediate deck board	4	1140 × 80 × 18
1	Lead & central deck board	3	1140 × 100 × 18


Nr.	Denomination	Number	Nominal dimensions
Nominal timber volume: 28,8 dm ³			CP5
Unit of measurement: mm Projection			
Wooden pallet 760 × 1140 mm			July 2017
			Edition: 7

Fastening pattern

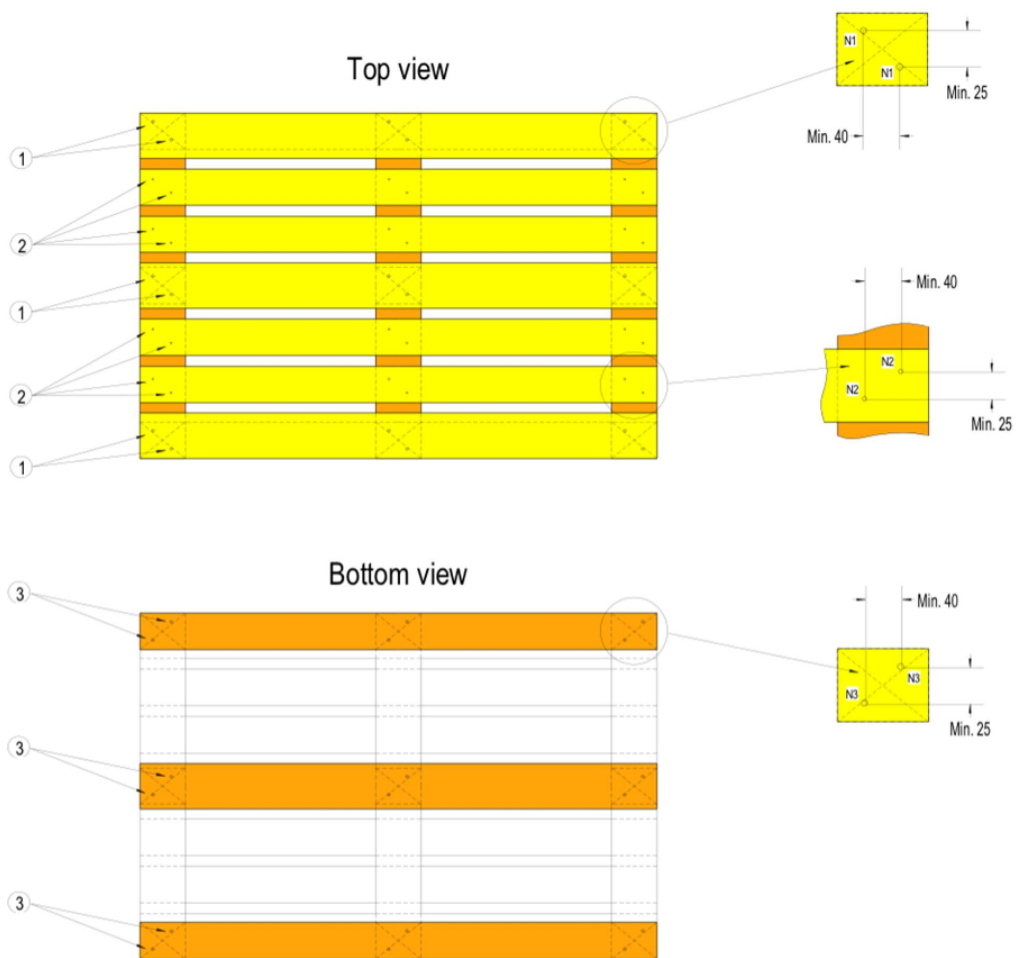


3	Lead & central bottom board - block	18 × N3
2	Intermediate deck board - stringer board	24 × N2
1	Lead & central deck board - stringer board - block	18 × N1
Position	Joint	Number
Unit of measurement: mm		CP5
Wooden pallet 760 × 1140 mm		
		July 2017
		Edition: 7

Design drawing

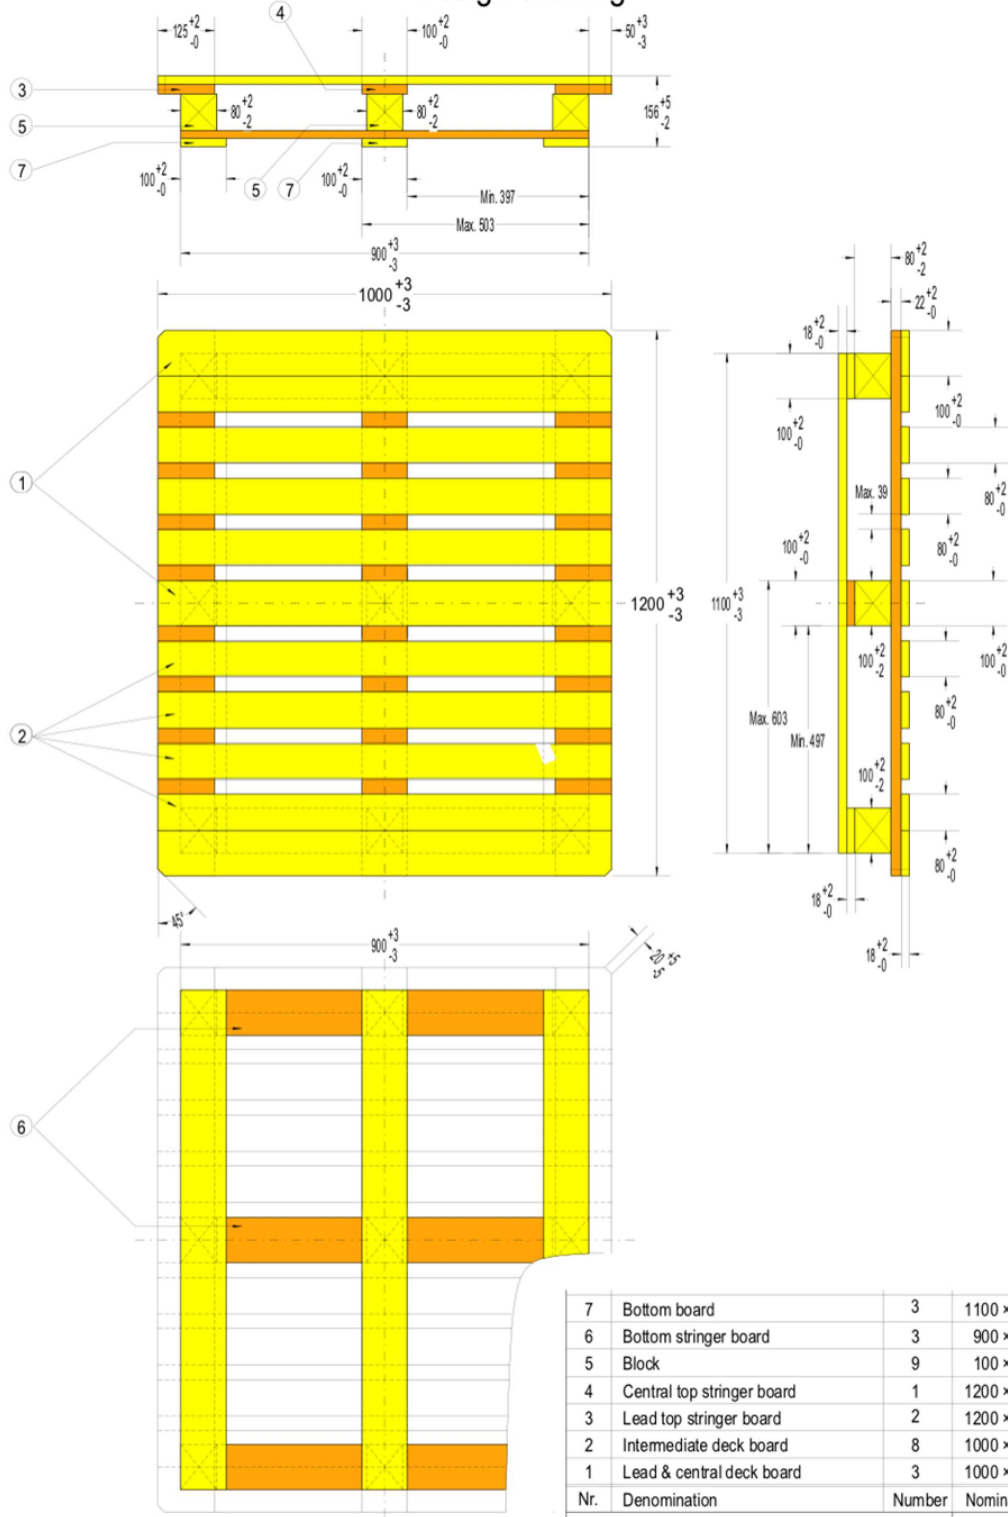

7	Bottom board	3	1100 × 100 × 18
6	Bottom stringer board	3	900 × 100 × 18
5	Block	9	100 × 80 × 80
4	Central top stringer board	1	1200 × 100 × 22
3	Lead top stringer board	2	1200 × 125 × 22
2	Intermediate deck board	8	1000 × 80 × 18
1	Lead & central deck board	3	1000 × 100 × 18
Nr.	Denomination	Number	Nominal dimensions
Nominal timber volume: 42,7 dm ³			CP6
Unit of measurement: mm		Projection	
Wooden pallet 1200 × 1000 mm			July 2017
			Edition: 7

Fastening pattern

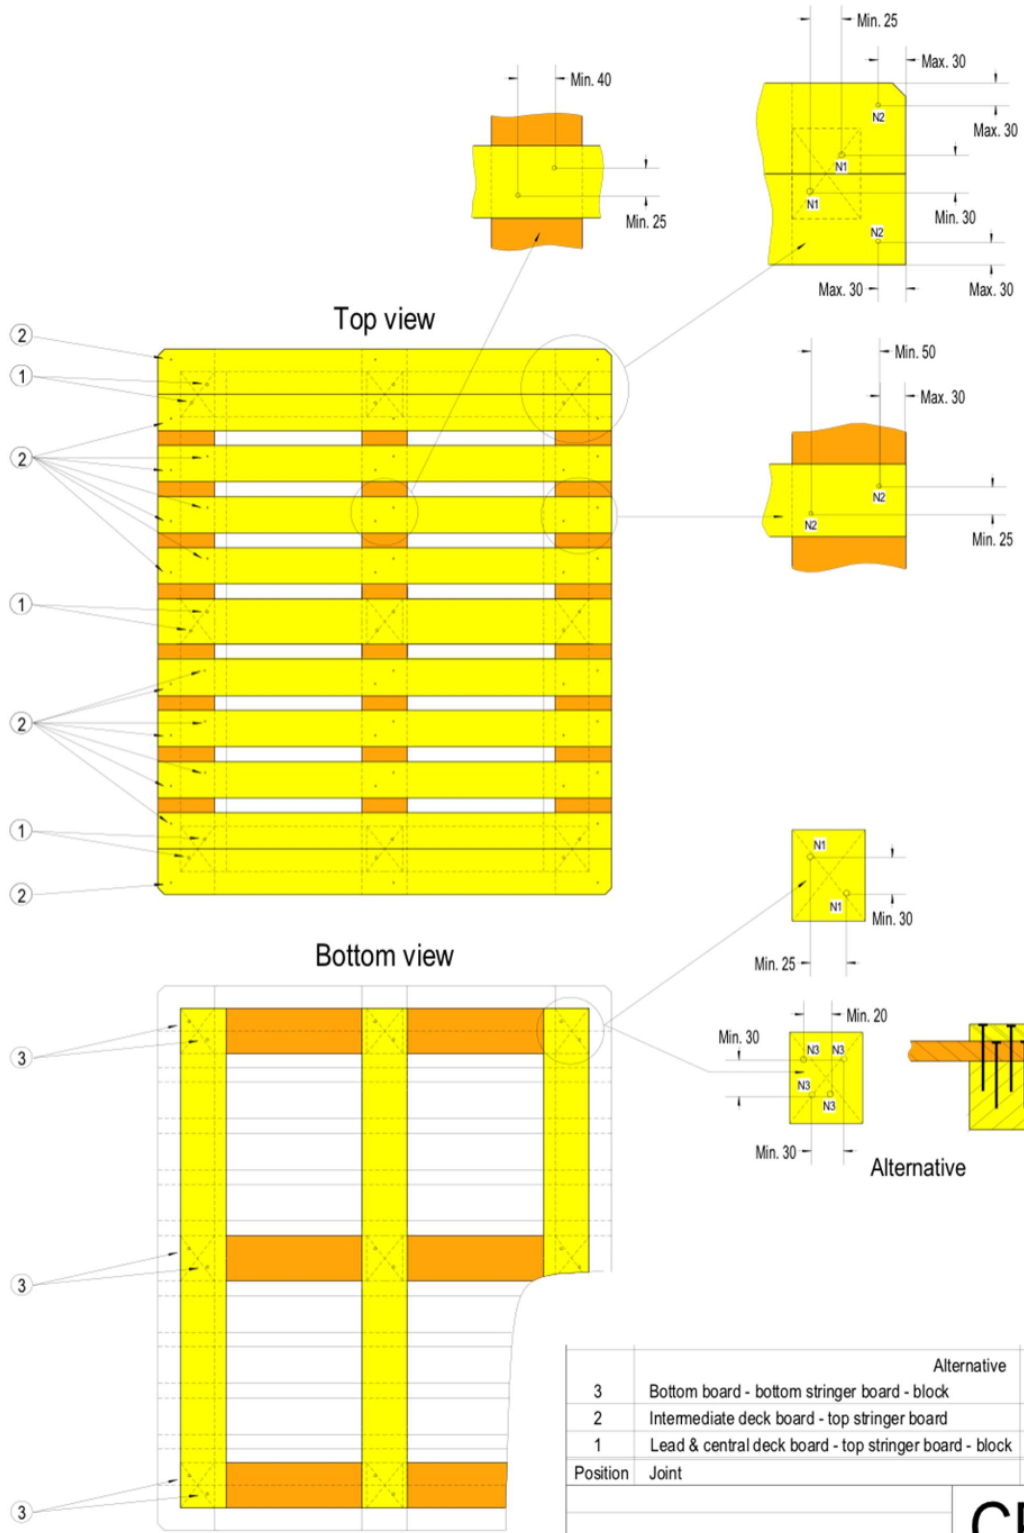


Position	Joint	Number
3	Bottom board - bottom stringer board - block	36 × N3 18 × N1
2	Intermediate deck board - top stringer board	48 × N2
1	Lead & central deck board - top stringer board - block	18 × N1
Alternative		36 × N3

Unit of measurement: mm

Wooden pallet 1200 × 1000 mm

CP6
July 2017
Edition: 7

Design drawing

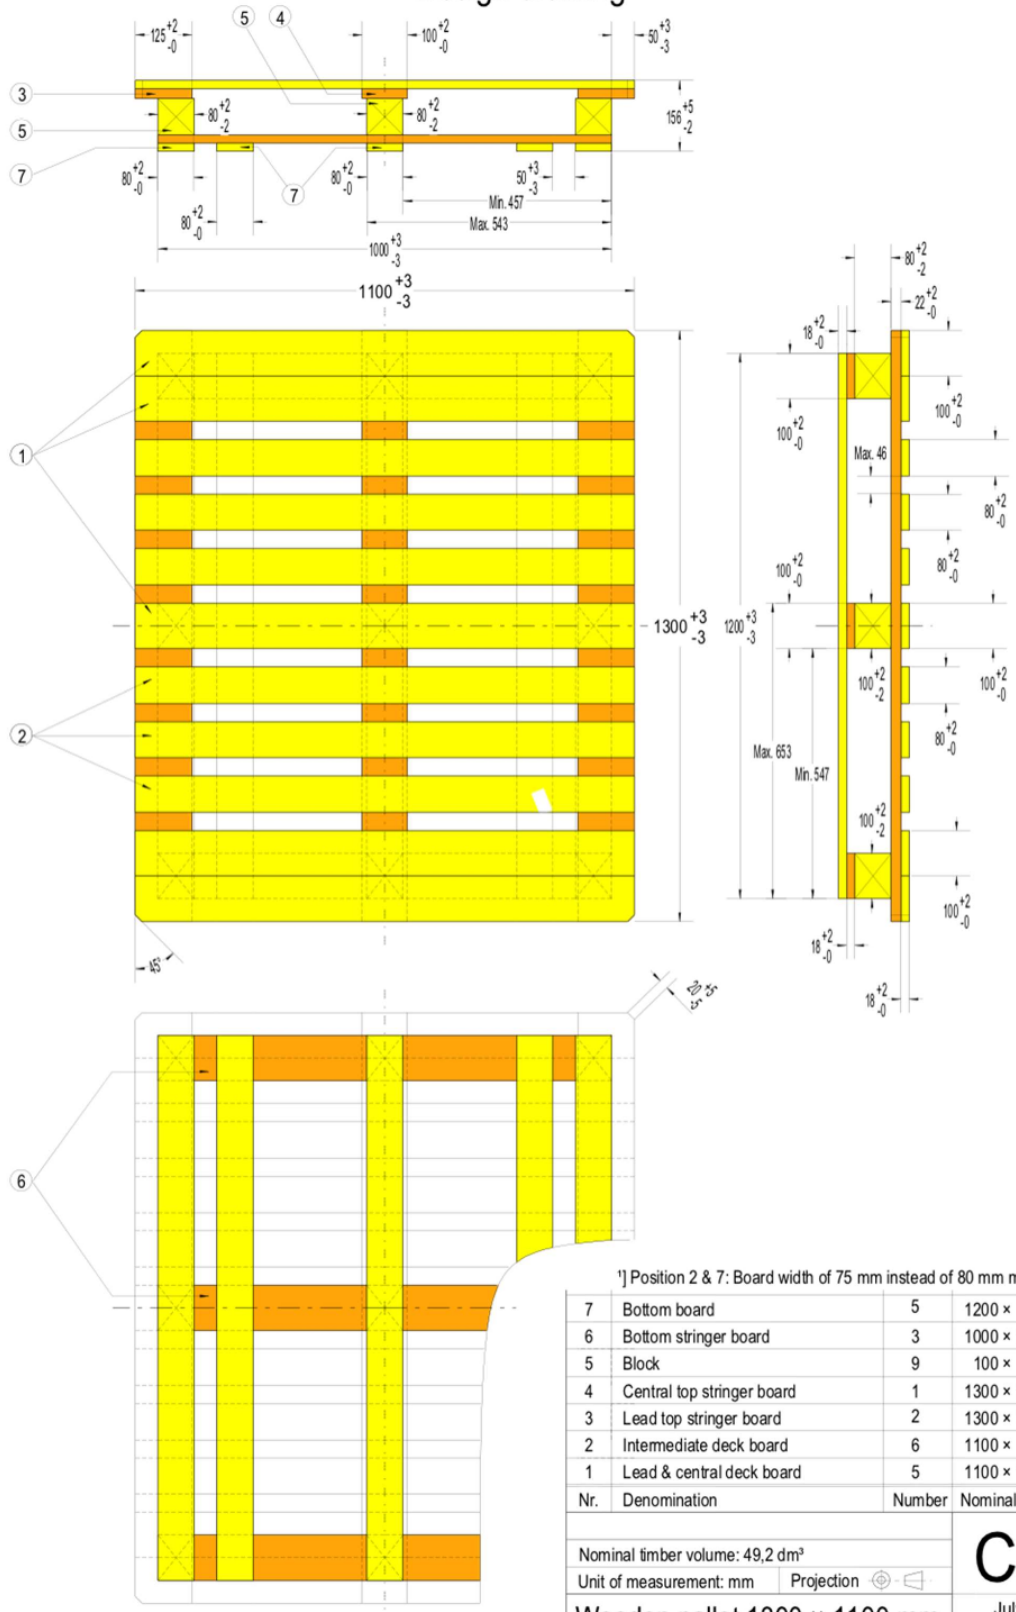

*) Position 2 & 7: Board width of 75 mm instead of 80 mm may be used.

7	Bottom board	5	1200 × 80 × 18 *)
6	Bottom stringer board	3	1000 × 100 × 18
5	Block	9	100 × 80 × 80
4	Central top stringer board	1	1300 × 100 × 22
3	Lead top stringer board	2	1300 × 125 × 22
2	Intermediate deck board	6	1100 × 80 × 18 *)
1	Lead & central deck board	5	1100 × 100 × 18


Nr.	Denomination	Number	Nominal dimensions
-----	--------------	--------	--------------------

Nominal timber volume: 49,2 dm³
 Unit of measurement: mm Projection

Wooden pallet 1300 × 1100 mm


CP7
 July 2017
 Edition: 7

Fastening pattern

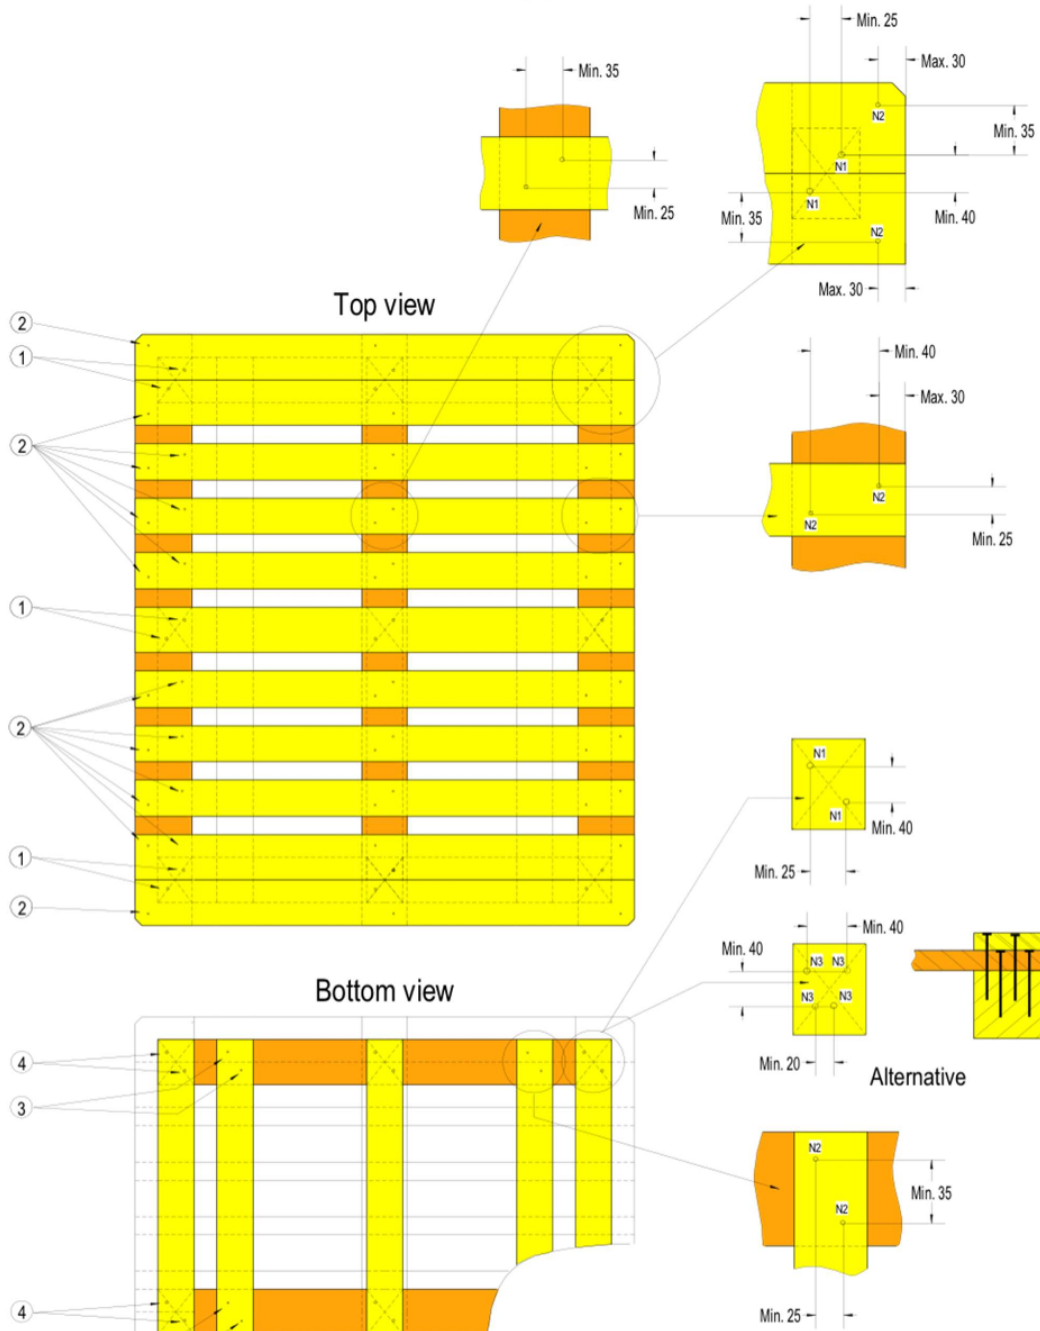

		Alternative	36 × N3
4	Lead & central bottom board - bottom stringer board - block		18 × N1
3	Intermediate bottom board - bottom stringer board		12 × N2
2	Intermediate deck board - top stringer board		48 × N2
1	Lead & central deck board - top stringer board - block		18 × N1
Position	Joint		Number
		CP7	
Unit of measurement: mm		July 2017	
Wooden pallet 1300 × 1100 mm		Edition: 7	

Design drawing

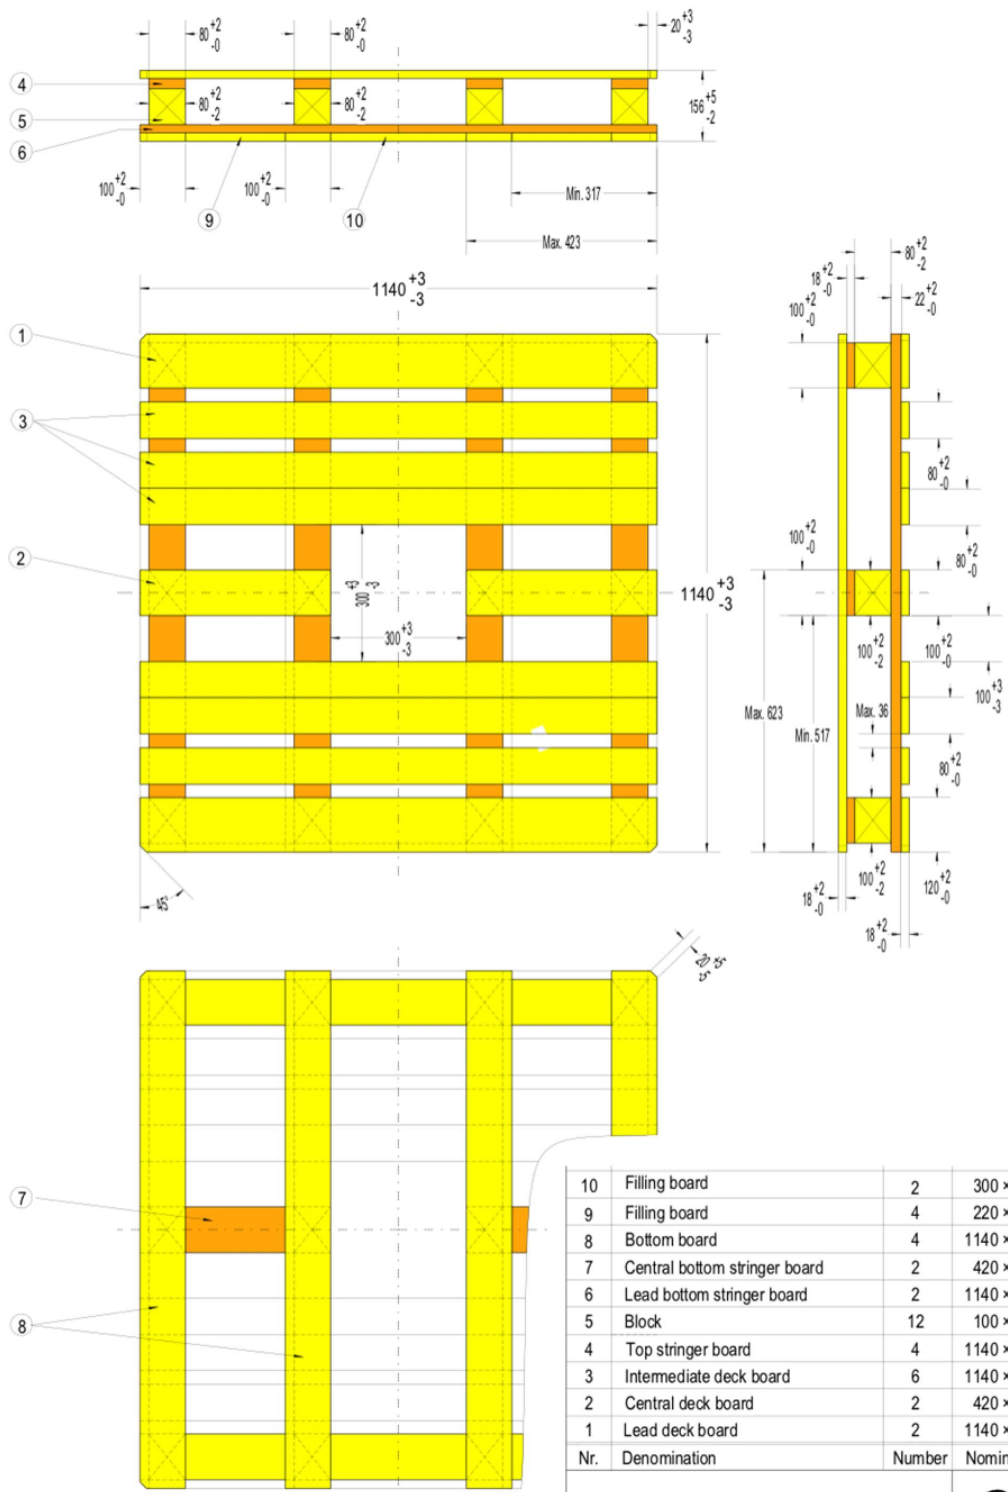

10	Filling board	2	300 × 100 × 18
9	Filling board	4	220 × 100 × 18
8	Bottom board	4	1140 × 100 × 18
7	Central bottom stringer board	2	420 × 100 × 18
6	Lead bottom stringer board	2	1140 × 100 × 18
5	Block	12	100 × 80 × 80
4	Top stringer board	4	1140 × 80 × 22
3	Intermediate deck board	6	1140 × 80 × 18
2	Central deck board	2	420 × 100 × 18
1	Lead deck board	2	1140 × 120 × 18


Nr.	Denomination	Number	Nominal dimensions
-----	--------------	--------	--------------------

Nominal timber volume: 48,5 dm³
 Unit of measurement: mm Projection


CP8
 July 2017
 Edition: 7

Wooden pallet 1140 × 1140 mm


Fastening pattern

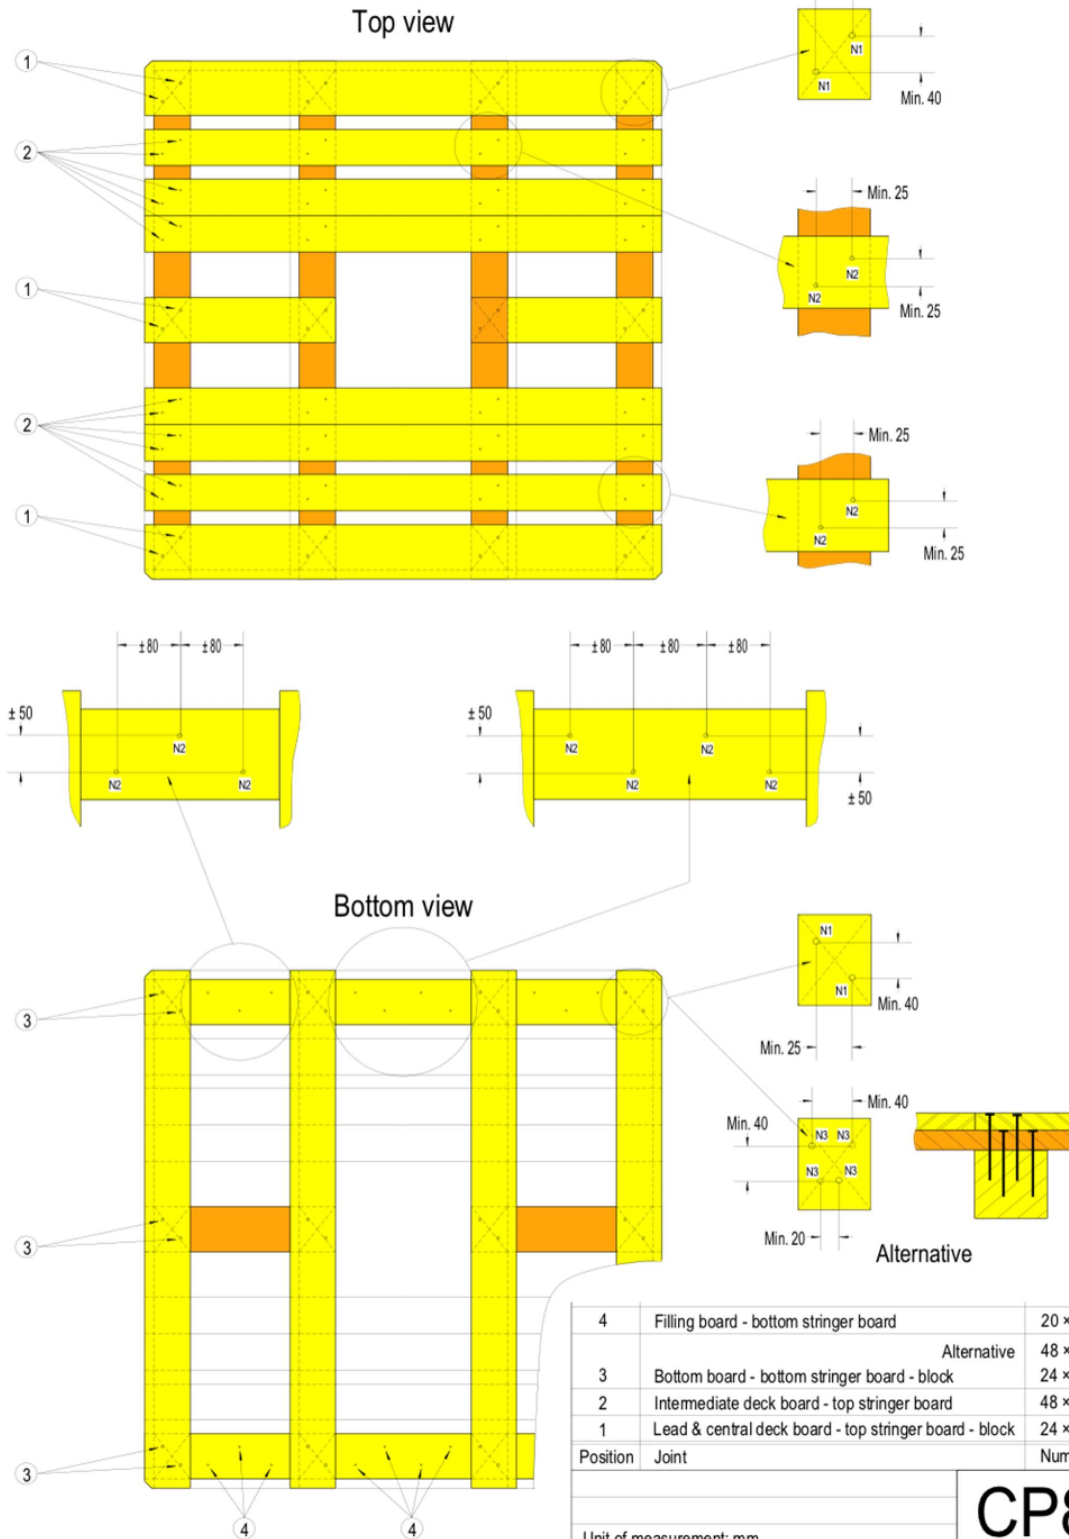

4	Filling board - bottom stringer board	20 × N2
	Alternative	48 × N3
3	Bottom board - bottom stringer board - block	24 × N1
2	Intermediate deck board - top stringer board	48 × N2
1	Lead & central deck board - top stringer board - block	24 × N1
Position	Joint	Number
		CP8
Unit of measurement: mm		July 2017
Wooden pallet 1140 × 1140 mm		Edition: 7

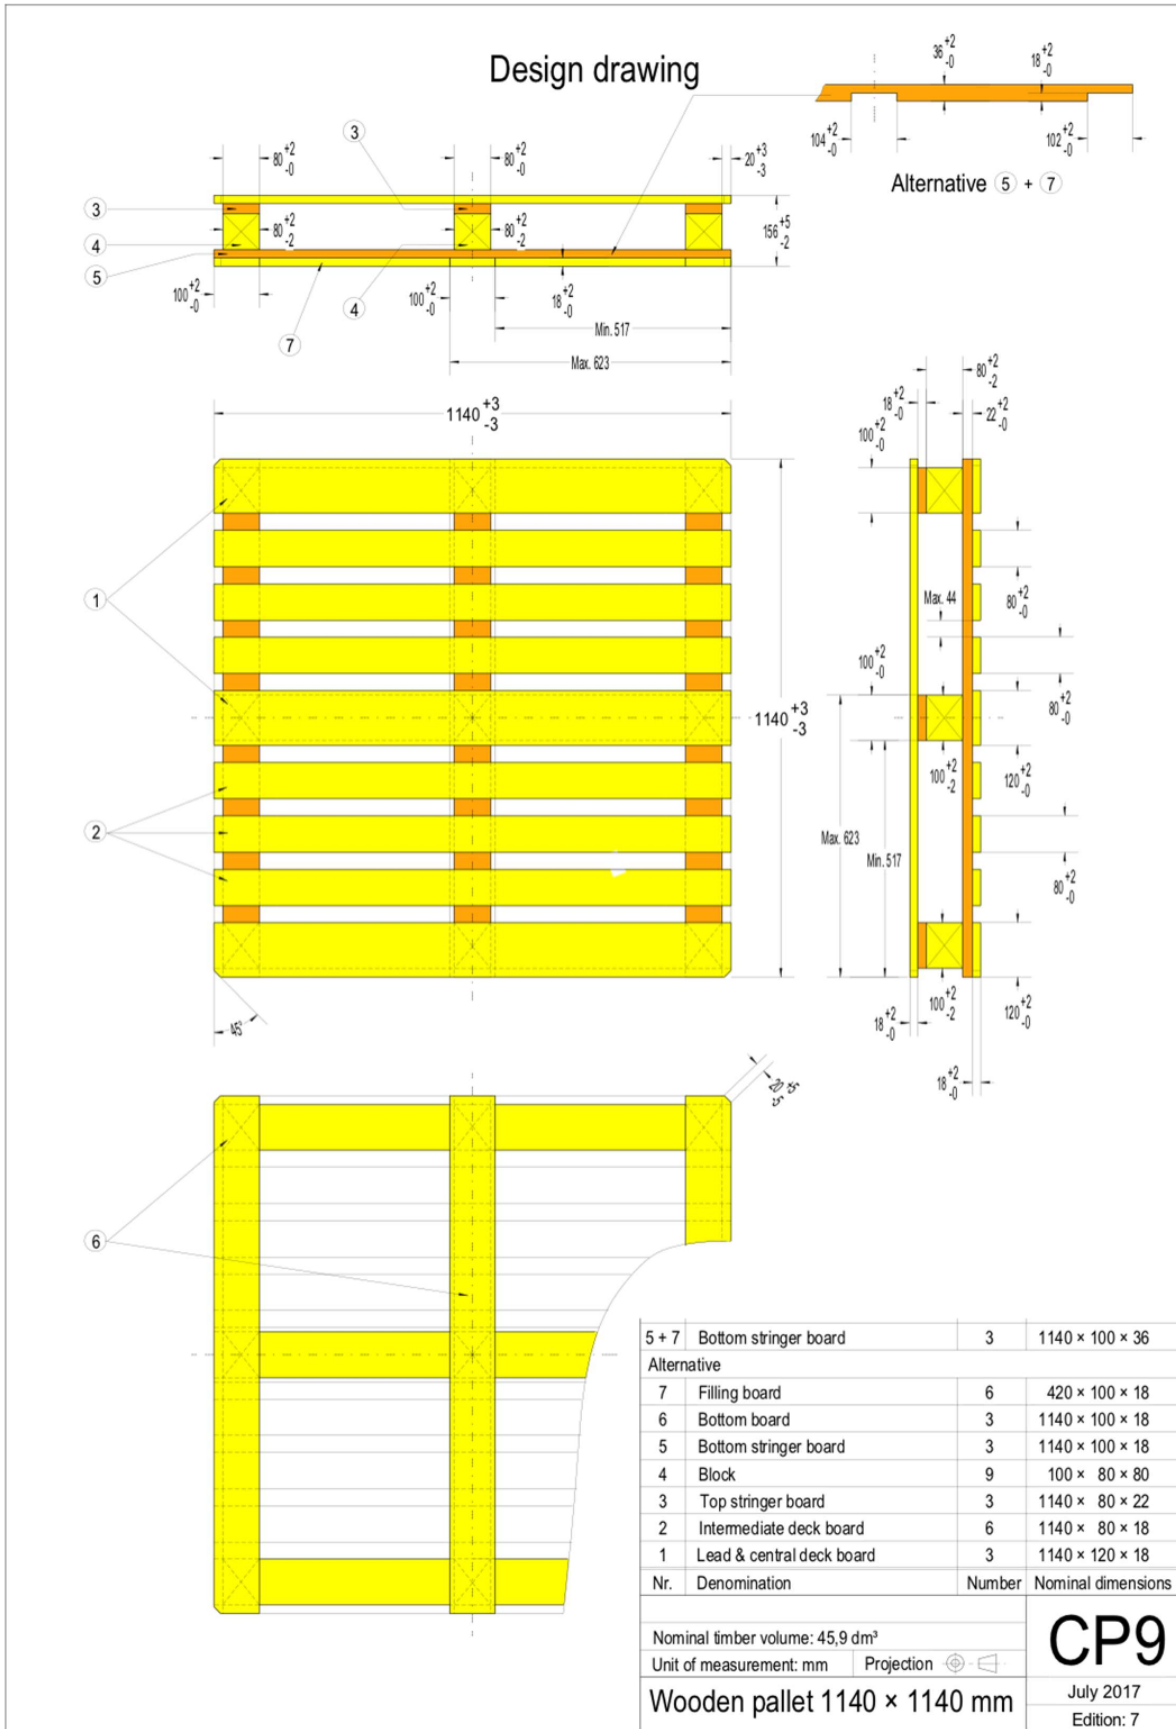

Fastening pattern

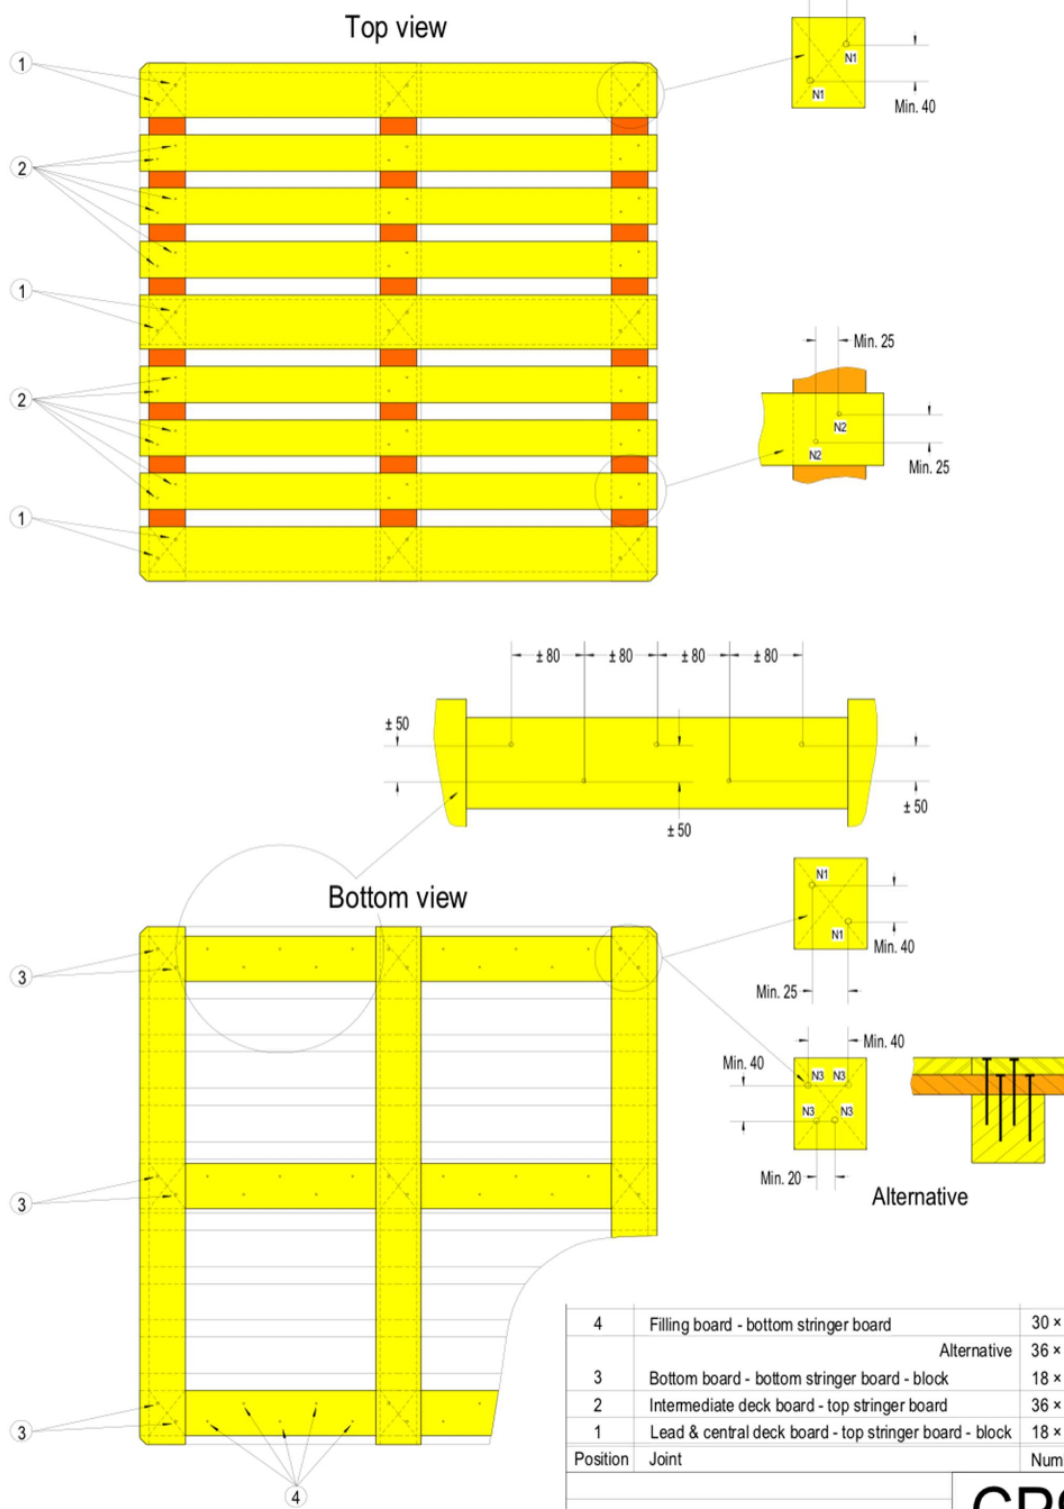

4	Filling board - bottom stringer board	30 × N2
		Alternative 36 × N3
3	Bottom board - bottom stringer board - block	18 × N1
2	Intermediate deck board - top stringer board	36 × N2
1	Lead & central deck board - top stringer board - block	18 × N1
Position	Joint	Number
		CP9
Unit of measurement: mm		July 2017
Wooden pallet 1140 × 1140 mm		Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality			Check the conformity	✓
Bark & bark pockets		None		
Wane	At the underside of intermediate deck boards	Height < 6 mm		
	At other components	None		
Knots	Intergrown or dead	< 30 mm		
	Loose	< 20 mm		
Deterioration	Mould or rot	None		
	Active insect infestation	None		

Pallet assembly & joints			Check the conformity	✓
Position of component parts		No missing or wrongly placed components		
Space between deck boards [after shrinkage of the timber]		≤ 38 mm		
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks		
Missing wood on boards		< ¼ of the board width		
		No fastener shank visible		
Warped boards		< ½ of the board thickness		
Missing wood on blocks		No fastener shank visible		
Number of fasteners	In lead & central deck boards	At least 3 × 3 in each deck board		
	In intermediate deck boards	At least 3 × 2 in each deck board		
	In bottom boards	At least 3 × 2 in each bottom board		
Placement of fasteners	Positioning	Not in the same fibre and spaced		
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface		
	Points protruding below the stringer boards	Bent back completely		
	Splits on boards without repair	None		
	Fasteners piercing the sides of blocks	None		
		Splits on blocks	None	

Pallet finishing & marking		Check the conformity	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks	Clearly legible		
	CP-design number burned into the middle block on both sides of the pallet		
	Manufacturer code & date burned into the middle block at least on one side		
	Repairer code & date stamped on a block on the right side [if applicable]		

Timber dimensions [after shrinkage]			Measure & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	95 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Stringer boards	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	133 mm			
	Width	74 mm			
	Height	74 mm			
Bottom boards	Width	128 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality		
YES		NO

Pallet dimensions			Measure & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1203 mm	1197 mm			
Width	1003 mm	997 mm			
Height	143 mm	129 mm			
Difference between diagonals	< 10 mm				

CP1
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality		Check the conformity of both pallets	✓
Bark & bark pockets		None	
Wane	At the underside of intermediate deck boards	Height < 6 mm	
	At other components	None	
Knots	Intergrown or dead	< 30 mm	
	Loose	< 20 mm	
Deterioration	Mould or rot	None	
	Active insect infestation	None	

Pallet assembly & joints		Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components	
Space between deck boards [after shrinkage of the timber]		≤ 41 mm	
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks	
Missing wood on boards		< ¼ of the board width	
		No fastener shank visible	
Warped boards		< ½ of the board thickness	
Missing wood on blocks		No fastener shank visible	
Number of fasteners	In lead & central deck boards	At least 3 × 2 in each deck board	
	In intermediate deck boards	At least 3 × 2 in each deck board	
	In bottom boards	At least 3 × 2 in each bottom board	
Placement of fasteners	Positioning	Not in the same fibre and spaced	
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface	
	Points protruding below the stringer boards	Bent back	
	Splits on boards without repair	None	
	Fasteners piercing the sides of blocks	None	
	Splits on blocks	None	

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	95 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Stringer boards	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	98 mm			
	Width	74 mm			
	Height	74 mm			
Bottom boards	Width	95 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y N	
Reference		
Inspector		
Date		
Acceptable quality		
YES NO		

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1203 mm	1197 mm			
Width	803 mm	797 mm			
Height	143 mm	129 mm			
Difference between diagonals	< 10 mm				

CP2
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality		Check the conformity of both pallets	✓
Bark & bark pockets		None	
Wane	At the underside of intermediate deck boards	Height < 6 mm	
	At other components	None	
Knots	Intergrown or dead	< 30 mm	
	Loose	< 20 mm	
Deterioration	Mould or rot	None	
	Active insect infestation	None	

Pallet assembly & joints		Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components	
Space between deck boards [after shrinkage of the timber]		≤ 49 mm	
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks	
Missing wood on boards		< ¼ of the board width	
		No fastener shank visible	
Warped boards		< ½ of the board thickness	
Missing wood on blocks		No fastener shank visible	
Number of fasteners	In lead & central deck boards	At least 3 × 3 in each deck board	
	In intermediate deck boards	At least 3 × 2 in each deck board	
	In bottom boards	At least 3 × 2 in each bottom board	
Placement of fasteners	Positioning	Not in the same fibre and spaced	
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface	
	Points protruding below the stringer boards	Bent back	
	Splits on boards without repair	None	
	Fasteners piercing the sides of blocks	None	
	Splits on blocks	None	

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	114 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Stringer boards	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	133 mm			
	Width	74 mm			
	Height	74 mm			
Bottom boards	Width	128 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality	YES NO	

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1143 mm	1137 mm			
Width	1143 mm	1137 mm			
Height	143 mm	129 mm			
Difference between diagonals	< 10 mm				

CP3
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality		Check the conformity of both pallets	✓
Bark & bark pockets		None	
Wane	At the underside of intermediate deck boards	Height < 6 mm	
	At other components	None	
Knots	Intergrown or dead	< 30 mm	
	Loose	< 20 mm	
Deterioration	Mould or rot	None	
	Active insect infestation	None	

Pallet assembly & joints		Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components	
Space between deck boards [after shrinkage of the timber]		≤ 56 mm	
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks	
Missing wood on boards		< ¼ of the board width	
		No fastener shank visible	
Warped boards		< ½ of the board thickness	
Missing wood on blocks		No fastener shank visible	
Number of fasteners	In lead & central deck boards	At least 3 × 3 in each deck board	
	In intermediate deck boards	At least 3 × 2 in each deck board	
	In bottom boards	At least 3 × 2 in each deck board	
Placement of fasteners	Positioning	Not in the same fibre and spaced	
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface	
	Points protruding below the stringer boards	Bent back	
	Splits on boards without repair	None	
	Fasteners piercing the sides of blocks	None	
	Splits on blocks	None	

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	114 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Stringer boards	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	118 mm			
	Width	74 mm			
	Height	74 mm			
Bottom boards	Width	114 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality		
YES		NO

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1303 mm	1297 mm			
Width	1103 mm	1097 mm			
Height	143 mm	129 mm			
Difference between diagonals	< 10 mm				

CP4
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality		Check the conformity of both pallets	✓
Bark & bark pockets		None	
Wane	At the underside of intermediate deck boards	Height < 6 mm	
	At other components	None	
Knots	Intergrown or dead	< 30 mm	
	Loose	< 20 mm	
Deterioration	Mould or rot	None	
	Active insect infestation	None	

Pallet assembly & joints		Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components	
Space between deck boards [after shrinkage of the timber]		≤ 34 mm	
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks	
Missing wood on boards		< ¼ of the board width	
		No fastener shank visible	
Warped boards		< ½ of the board thickness	
Missing wood on blocks		No fastener shank visible	
Number of fasteners	In deck boards	At least 3 × 2 in each deck board	
	In bottom boards	At least 3 × 2 in each bottom board	
Placement of fasteners	Positioning	Not in the same fibre and spaced	
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface	
	Points protruding below the stringer boards	Bent back	
	Splits on boards without repair	None	
	Fasteners piercing the sides of blocks	None	
Splits on blocks		None	

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing	Square edged		
	Clean cut		
Corner chamfers		Absent	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	95 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Stringer boards	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	98 mm			
	Width	74 mm			
	Height	74 mm			
Lead bottom boards	Width	76 mm			
	Thickness	17 mm			
Central bottom board	Width	95 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality		
YES		NO

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1143 mm	1137 mm			
Width	763 mm	757 mm			
Height	143 mm	129 mm			
Difference between diagonals	< 10 mm				

CP5
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality			Check the conformity of both pallets	✓
Bark & bark pockets		None		
Wane	At the underside of intermediate deck boards	Height < 5 mm		
	At other components	None		
Knots	Intergrown or dead	< 30 mm		
	Loose	< 20 mm		
Deterioration	Mould or rot	None		
	Active insect infestation	None		

Pallet assembly & joints			Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components		
Space between deck boards [after shrinkage of the timber]		≤ 43 mm		
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks		
Missing wood on boards		< ¼ of the board width		
		No fastener shank visible		
Warped boards		< ½ of the board thickness		
Missing wood on blocks		No fastener shank visible		
Number of fasteners	In deck boards	At least 3 × 2 in each deck board		
	In bottom boards	At least 3 × 2 in each bottom board		
Placement of fasteners	Positioning	Not in the same fibre and spaced		
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface		
	Points protruding below the stringer board	Bent back		
	Splits on boards without repair	None		
	Fasteners piercing the sides of blocks	None		
	Splits on blocks	None		

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	95 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Lead top stringer boards	Width	119 mm			
	Thickness	21 mm			
Central top stringer board	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	98 mm			
	Width	74 mm			
	Height	74 mm			
Bottom stringer boards	Width	95 mm			
	Thickness	17 mm			
Bottom boards	Width	95 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality		
YES NO		

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1203 mm	1197 mm			
Width	1003 mm	997 mm			
Height	161 mm	146 mm			
Difference between diagonals	< 10 mm				

CP6
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality		Check the conformity of both pallets	✓
Bark & bark pockets		None	
Wane	At the underside of intermediate deck boards	Height < 5 mm	
	At other components	None	
Knots	Intergrown or dead	< 30 mm	
	Loose	< 20 mm	
Deterioration	Mould or rot	None	
	Active insect infestation	None	

Pallet assembly & joints		Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components	
Space between deck boards [after shrinkage of the timber]		≤ 51 mm*	
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks	
Missing wood on boards		< ¼ of the board width	
		No fastener shank visible	
Warped boards		< ½ of the board thickness	
Missing wood on blocks		No fastener shank visible	
Number of fasteners	In deck boards	At least 3 × 2 in each deck board	
	In bottom boards	At least 3 × 2 in each bottom board	
Placement of fasteners	Positioning	Not in the same fibre and spaced	
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface	
	Points protruding below the stringer board	Bent back	
	Splits on boards without repair	None	
	Fasteners piercing the sides of blocks	None	
	Splits on blocks	None	

*] ≤ 54 mm if nominal dimension of 75 mm has been used

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	95 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm*			
	Thickness	17 mm			
Lead top stringer boards	Width	119 mm			
	Thickness	21 mm			
Central top stringer board	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	98 mm			
	Width	74 mm			
	Height	74 mm			
Bottom stringer boards	Width	95 mm			
	Thickness	17 mm			
Bottom boards	Width	76 mm*			
	Thickness	17 mm			

*] 71 mm if nominal dimension of 75 mm has been used

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1303 mm	1297 mm			
Width	1103 mm	1097 mm			
Height	161 mm	146 mm			
Difference between diagonals	< 10 mm				

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality		
YES NO		

CP7
July 2017
Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality			Check the conformity of both pallets	✓
Bark & bark pockets		None		
Wane	At the underside of intermediate deck boards	Height < 5 mm		
	At other components	None		
Knots	Intergrown or dead	< 30 mm		
	Loose	< 20 mm		
Deterioration	Mould or rot	None		
	Active insect infestation	None		

Pallet assembly & joints			Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components		
Space between deck boards [after shrinkage of the timber]		≤ 40 mm		
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks		
Missing wood on boards		< ¼ of the board width		
		No fastener shank visible		
Warped boards		< ½ of the board thickness		
Missing wood on blocks		No fastener shank visible		
Number of fasteners	In deck boards	At least 3 × 2 in each deck board		
	In bottom boards	At least 3 × 2 in each bottom board		
	In filling boards	At least 3 in each short and 4 in each long filling board		
Placement of fasteners	Positioning	Not in the same fibre and spaced		
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface		
	Points protruding below the stringer board	Bent back		
	Splits on boards without repair	None		
	Fasteners piercing the sides of blocks	None		
		Splits on blocks	None	

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing	Square edged		
	Clean cut		
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks	Easily legible		
	CP-design number burned into the middle block on both sides of the pallet		
	Manufacturer code & date burned into the middle block at least on one side		
	Repairer code & date stamped on a block on the right side [if applicable]		

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead deck boards	Width	114 mm			
	Thickness	17 mm			
Central deck boards	Width	95 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Top stringer boards	Width	76 mm			
	Thickness	21 mm			
Blocks	Length	98 mm			
	Width	74 mm			
	Height	74 mm			
Bottom stringer boards, bottom boards & filling boards	Width	95 mm			
	Thickness	17 mm			

Manufacturer code		
Reconditioned pallets	Y	N
Reference		
Inspector		
Date		
Acceptable quality	YES NO	

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1143 mm	1137 mm			
Width	1143 mm	1137 mm			
Height	161 mm	146 mm			
Difference between diagonals	< 10 mm				

CP8
July 2017 Edition: 7

Inspection report

Check two pallets.

Critical safety item

Timber quality		Check the conformity of both pallets	✓
Bark & bark pockets		None	
Wane	At the underside of intermediate deck boards	Height < 5 mm	
	At other components	None	
Knots	Intergrown or dead	< 30 mm	
	Loose	< 20 mm	
Deterioration	Mould or rot	None	
	Active insect infestation	None	

Pallet assembly & joints		Check the conformity of both pallets	✓
Position of component parts		No missing or wrongly placed components	
Space between deck boards [after shrinkage of the timber]		≤ 49 mm	
Grain direction of natural timber blocks		Parallel to the longitudinal measure of the blocks	
Missing wood on boards		< ¼ of the board width	
		No fastener shank visible	
Warped boards		< ½ of the board thickness	
Missing wood on blocks		No fastener shank visible	
Number of fasteners	In deck boards	At least 3 × 2 in each deck board	
	In bottom boards	At least 3 × 2 in each bottom board	
	In filling boards [if applicable]	At least 5 in each filling board	
Placement of fasteners	Positioning	Not in the same fibre and spaced	
	Nail heads [after shrinkage of the timber]	Below or flush to the board surface	
	Points protruding below the stringer board	Bent back	
	Splits on boards without repair	None	
	Fasteners piercing the sides of blocks	None	
	Splits on blocks	None	

Pallet finishing & marking		Check the conformity of both pallets	✓
General aspect		Clean and free of contaminants	
Timber sawing		Square edged	
		Clean cut	
Length of corner chamfers		15 - 25 mm	
Marking of natural timber or particleboard blocks		Easily legible	
		CP-design number burned into the middle block on both sides of the pallet	
		Manufacturer code & date burned into the middle block at least on one side	
		Repairer code & date stamped on a block on the right side [if applicable]	

Timber dimensions [after shrinkage]			Measure both pallets & check the conformity		
Component	Measure	Minimum	Pallet 1	Pallet 2	✓
Lead & central deck boards	Width	114 mm			
	Thickness	17 mm			
Intermediate deck boards	Width	76 mm			
	Thickness	17 mm			
Top stringer boards	Width	95 mm			
	Thickness	21 mm			
Blocks	Length	98 mm			
	Width	74 mm			
	Height	74 mm			
Bottom stringer boards, filling boards & bottom boards	Width	95 mm			
	Thickness	17 mm			
Alternative bottom stringer boards [if applicable]	Width	95 mm			
	Thickness	34 mm			

Manufacturer code	
Reconditioned pallets	Y N
Reference	
Inspector	
Date	
Acceptable quality	
YES NO	

Pallet dimensions			Measure both pallets & check the conformity		
Measure	Maximum	Minimum	Pallet 1	Pallet 2	✓
Length	1143 mm	1137 mm			
Width	1143 mm	1137 mm			
Height	161 mm	146 mm			
Difference between diagonals	< 10 mm				

CP9
July 2017
Edition: 7